

Nanotechnology in Textiles

Ali K. Yetisen,^{*,†,‡} Hang Qu,[§] Amir Manbachi,^{‡,⊥} Haider Butt,^{||} Mehmet R. Dokmeci,^{‡,⊥,¶}
Juan P. Hinestroza,[#] Maksim Skorobogatiy,[§] Ali Khademhosseini,^{‡,⊥,¶,△,▲} and Seok Hyun Yun^{*,†,‡}

[†]Harvard Medical School and Wellman Center for Photomedicine, Massachusetts General Hospital, 65 Landsdowne Street, Cambridge, Massachusetts 02139, United States

[‡]Harvard–MIT Division of Health Sciences and Technology, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, United States

[§]Department of Engineering Physics, École Polytechnique de Montréal, Montréal, Québec H3T 1J4, Canada

[⊥]Biomaterials Innovation Research Center, Division of Biomedical Engineering, Brigham and Women's Hospital, Harvard Medical School, Cambridge, Massachusetts 02139, United States

^{||}Nanotechnology Laboratory, School of Engineering Sciences, University of Birmingham, Birmingham B15 2TT, United Kingdom

[¶]Wyss Institute for Biologically Inspired Engineering, Harvard University, Boston, Massachusetts 02115, United States

[#]Department of Fiber Science, College of Human Ecology, Cornell University, Ithaca, New York 14850, United States

[△]Department of Physics, King Abdulaziz University, Jeddah, Saudi Arabia

[▲]Department of Bioindustrial Technologies, College of Animal Bioscience and Technology, Konkuk University, Hwayang-dong, Gwangjin-gu, Seoul 143-701, Republic of Korea

ABSTRACT: Increasing customer demand for durable and functional apparel manufactured in a sustainable manner has created an opportunity for nanomaterials to be integrated into textile substrates. Nanomaterials can induce stain repellence, wrinkle-freeness, static elimination, and electrical conductivity to fibers without compromising their comfort and flexibility. Nanomaterials also offer a wider application potential to create connected garments that can sense and respond to external stimuli *via* electrical, color, or physiological signals. This review discusses electronic and photonic nanotechnologies that are integrated with textiles and shows their applications in displays, sensing, and drug release within the context of performance, durability, and connectivity. Risk factors including nanotoxicity, nanomaterial release during washing, and environmental impact of nanotextiles based on life cycle assessments have been evaluated. This review also provides an analysis of nanotechnology consolidation in the textiles market to evaluate global trends and patent coverage, supplemented by case studies of commercial products. Perceived limitations of nanotechnology in the textile industry and future directions are identified.

KEYWORDS: nanotechnology, fashion, fabrics, fibers, nanoparticles, carbon nanotubes, graphene, energy storage, fiber optics, nanotoxicity



The concept of clothing is undergoing a transformation through innovation in wearable technologies. Intelligent clothing has an increasing presence in prominent fashion weeks in New York, London, and Paris. Fashion designers are creating functional materials and integrating emerging communication devices, flexible electronics, and nanomaterials to garments and designer clothes. For example, Philips designed a dress (*Bubelle*) that can tune its colors based on the wearer's mood. Black Eyed Peas has also embraced technology on the stage; for example, they used organic light-emitting diode (OLED)-based clothing and adaptive materials in their performances. Fashion and technology company Studio XO has created a "digital mermaid bra", whose crystals sparked

in time to Azealia Banks' real-time rapping. Recently, TechHaus, the technical division of Haus of Gaga, has created a series of performance dresses for Lady Gaga's ARTPOP campaign (2013). Gaga's featured artworks included a three-dimensional (3D)-printed bubble machine dress (*Anemone*), a Jeff Koons-inspired design called the Parametric Sculpture Dress, a piece with animated black mirrors (*Cipher*), and a flying drone dress (*Volantis*). Singers, artists, designers, and fashion icons have directed their interest to new materials that

Received: December 28, 2015

Accepted: February 9, 2016

can stand out in public events and media. The designers that have pioneered the use of technology in fashion include Ralph Lauren, Diane von Furstenberg, Hussein Chalayan, Zac Posen, Rebecca Minkoff, Richard Nicoll, and Iris van Herpen.

Cotton is a widely used fiber type that exhibits high absorbency, softness, and breathability. However, the use of cotton in nonclassical applications is limited since its fibers have relatively low strength, low durability, easy creasing and soiling, and flammability.¹ Synthetic fibers can be antimicrobial and stain/crease-resistant but generally lack comfort as compared to cotton. The development of new fiber types that combine the advantages of both natural and synthetic fibers, as well as offering novel functions, has been desirable since the 1940s.² Customer demand for improved appearance color, shape, texture, and functionality has also increased.³ Flexible electronics and optical devices can be integrated into textiles.¹ The applications of the functionalized textiles include medical monitoring of body function and metabolism,^{4,5} rehabilitation,⁶ and electronic devices integrated into clothes.⁷ Furthermore, these technologies allow integrating sensors into textiles.⁸

A new frontier in clothing technology is nanoengineered functional textiles.^{9–11} The advantage of nanomaterials concerns creating function without altering the comfort properties of the substrate.¹² Textile is an universal interface and ideal substrate for the integration of nanomaterials, electronics, and optical devices. Such integrated materials and technologies offer a platform that responds to mechanical, chemical, electrical, thermal, optical, or magnetic stimuli. Such wearable devices may include sensors, data transmission, and processing units. These engineered materials should seamlessly integrate into garments and be flexible and comfortable while having no allergic reaction to the body. Additionally, such materials need to satisfy weight, performance, and appearance properties (color). A significant challenge in the textile industry is that conventional approaches to functionalize fabrics do not lead to permanent effects. For example, laundering decreases imparted functional effects. Hence, nanotechnology can play a part in introducing new and permanent functions to fabrics. Textiles can be nanoengineered to have specific functions including hydrophobicity, antibacterial properties, conductivity, antiwrinkle properties, antistatic behavior, and light guidance and scattering (Figure 1). Using nanotechnology, these properties can be achieved without affecting breathability or texture. Such materials may be in the form of surface coatings, voided patterns, fillers, or foams.

NANOENGINEERED TEXTILES

Water and Oil Repellence. Water repellence can be imparted to textiles by forming nanowhiskers consisting of hydrocarbons that are 3 orders of magnitude smaller than a typical cotton fiber. Nanowhiskers are integrated within the fabric to create a peach fuzz effect.¹³ Analogous to the Lotus effect, the spaces between individual whiskers are smaller than a drop of water but larger than water molecules, producing a high surface tension that allows the water to remain on the surface.^{14,15} The whiskers maintain breathability as they permeate gases. Water repellence can also be induced through creation of 3D surface structures on the fabric by adding gel-forming additives or coating the textile with nanoparticulate film.¹⁶ For example, audio frequency plasma of fluorocarbon derivatives can be applied to coat cotton fibers with nanoparticulates.¹⁷ By producing roughness on the surface of the fabric, superhydrophobicity can be created without affecting



Figure 1. Applications of nanotechnology in textiles.

abrasion resistance and softness of the fabric. Silica (SiO_2) nanoparticles (NPs) in combination with water-repellent agents can also be utilized to impart hydrophobicity to textiles.¹⁸ SiO_2 NPs (143–378 nm) were synthesized *via* a sol–gel process. Cotton fabrics treated with both SiO_2 NPs and water-repellent agent produced contact angles above 130° . SiO_2 NPs could be coated over cotton in the presence of perfluorooctylated quaternary ammonium silane coupling agent (PQASCA) to produce hydrophobicity.¹⁹ While the SiO_2 NPs create roughness on the surface of cotton fibers, PQASCA lowered the surface energy. The resulting textiles exhibited water repellence with a water contact angle of 145° . Oil repellency of the fabric also improved, showing a 131° contact angle for a diiodomethane (CH_2I_2) droplet on the fabric surface. In another study, amphiphilic Janus micro/NPs were chemically immobilized on textile surfaces.²⁰ While microparticles bound between fibers, NPs attached to the fiber surface. Janus particle immobilized textiles showed water repellence.

Bioinspired design has also motivated the investigation of water-repellent materials. For example, duck feathers consist of multiscale structures having preening oil to repel water. The microstructure of duck feathers was simulated by coating cotton and polyester textiles with chitosan using a surface solution precipitation method followed by modification with a silicone compound to achieve a low surface energy.²¹ Figure 2a shows a scanning electron microscope (SEM) image of polyester and chitosan-treated polyester having nanosized roughness on the surface. Chitosan-treated polyester textiles provided flexibility and water repellence. Lotus leaf nanostructures also inspired biomimetic studies for application in textiles.²² Cotton fibers were coated with pristine and surface-modified carbon nanotubes (CNTs) to mimic the nanostructure of lotus leaves. The resulting cotton fabrics had contact angles greater than 150° . Another study that was inspired from lotus leaves involved the development of a nanocoating (20 nm) to create hydrophobic textiles.²³ The nanocoating consisted of epoxy-containing poly(glycidyl methacrylate)

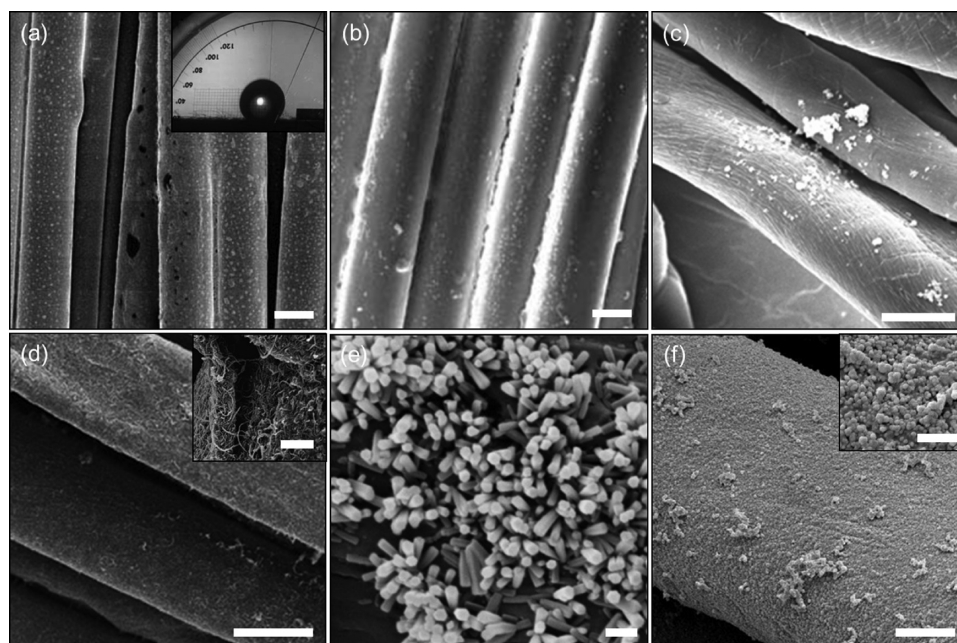


Figure 2. SEM images of nanoparticle-functionalized fibers. (a) Water repellence: chitosan-treated polyester with nanoscale roughness on the surface. Scale bar = 10 μm . The inset shows the profile of a water droplet on the treated polyester fabric. Reprinted with permission from ref 21. Copyright 2008 IOP Publishing. (b) Antistatic properties: polyester fiber surfaces treated with NPs and fluorine. Scale bar = 20 μm . Reprinted with permission from ref 24. Copyright 2011 Sage Publications. (c) Wrinkle resistance: cotton fibers treated with 1,2,3,4-BCTA and TiO_2 NPs. Scale bar = 10 μm . Reprinted with permission from ref 25. Copyright 2010 Springer Publishing. (d) Strength enhancement: CNT-coated cotton fibers. Scale bar = 10 μm . Reprinted with permission from ref 26. Copyright 2008 The Royal Society of Chemistry. The inset shows the magnified view of the fiber surface. Inset scale bar = 1 μm . (e) UV blocking: ZnO nanorods grown on cotton fibers. Scale bar = 300 nm. Reprinted from ref 27. Copyright 2005 American Chemical Society. (f) Antibacterial properties and odor control: cotton fibers treated with Ag NPs. Scale bar = 5 μm . The inset shows the magnified Ag NPs on the surface. Inset scale bar = 1 μm . Reprinted with permission from ref 28. Copyright 2012 Elsevier.

(PGMA) and SiO_2 NPs for the initial surface modification and generation of the primary reactive layer. Polymers with different functional groups (e.g., carboxy, anhydride, amino, and hydroxyl) could be grafted on the reactive layer.

Oil-repellent textiles have also been produced. Polyester fabric could be coated with silicone nanofilaments and treated with plasma fluorination to impart superoleophobic properties to textiles.²⁹ The produced fabric samples had an oil repellency grade of 8 and repelled alkanes. Hydrophobic and oleophobic properties could be simultaneously imparted to textiles. For example, cotton fibers were impregnated with SiO_2 particles to produce a dual-size surface roughness, followed by hydrophobization with poly(dimethylsiloxane) (PDMS), resulting in a static water contact angle of 155° for a droplet.³⁰ To induce oleophobicity, the SiO_2 particles on the fibers were treated with a perfluoroalkyl chain, which was demonstrated by a static contact angle of 140° and a roll-off angle of 24° for oil droplets.

Antistatic Properties. Synthetic fibers such as polyester and nylon have high static charge because they are not hydrophilic. On the other hand, cellulosic fibers limit the static charges due to their high moisture content. TiO_2 NPs,³¹ ZnO whiskers,³² and antimony (Sb)-doped tin oxide (SnO_2) particles³³ were utilized to impart antistatic properties to synthetic fibers. These materials are electrically conductive and dissipate the static charge accumulated on the textile. Additionally, silane nanosol enhances antistatic properties, as it absorbs moisture in the air through hydroxyl groups.³⁴ In commercial products, poly(tetrafluoroethylene) (PTFE) (W. L. Gore) developed an antistatic membrane that consisted of electrically conductive NPs anchored in the fibrils of the

membrane.³⁵ This membrane limited the formation of isolated chargeable areas and voltage peaks. This approach is advantageous over other antistatic agents since it does not wash off during laundry. Sol–gel coatings could be applied as a surface treatment to impart antistatic properties combined with hydrophobic properties.³⁶ Sol–gel composition consisted of hydrophobic compounds such as alkoxysilanes modified with alkyl chains and hydrophilic compounds including amino-functionalized alkoxysilanes. This combination allowed formation of hydrophobic groups at the fiber–air interface, while the deeper regions were hydrophilic. Sol–gel-coated textiles had water repellence but contained humidity in deeper regions of the coatings to produce antistatic properties. Antistatic charges with hydrophobicity could be achieved by treating polyester fabric with silver (Ag) NPs and fluorine water-repellent finish (Figure 2b).²⁴ After 10 washings, the polyester fabric had FTTS-FA-009 A grade antistatic property and AATCC 22 spray rating 90 grade for its hydrophobic quality.

ZnO NPs have been utilized to produce antistatic properties.³⁷ ZnO NPs, prepared by direct precipitation using zinc chloride (ZnCl_2), were immobilized on polyester fabrics through a pad-dry-cure process with an antistatic finishing agent. The charge density of polyester fabrics was reduced from 58 to 0.95 (units in $\times 10^{-7} \text{ C m}^{-2}$). As the concentration of ZnO NPs increased in the finishing agent, the antistatic property of the fabric decreased due to reduced dispersion of NPs. Additionally, the addition of Ag NPs decreased the static voltage of polyester fabric by 60.4%.³⁸ The combination of Ag, gold (Au), and Zn oxide particles decreased the static voltage by 77.7%. In another study, Sb-NP-doped SnO_2 particles were

utilized to impart antistatic properties to polyacrylonitrile (PAN) fibers.³⁹ These particles were dispersed in water using polyethylenimine (PEIN), and this solution was added to the preheating bath during spinning of PAN fibers. The particles diffused into the fibers created electrically conductive channels, which produced antistatic properties.

Wrinkle Resistance. Cellulose molecules in the cotton linearly organize themselves passing through the crystalline and amorphous sections of the fibers. Hydrogen bonds hold together cellulose molecules in their positions. Upon applying a force to the fibers, the cellulose chains displace from their original positions and hydrogen bonds re-form at new locations. Nanocoatings that prevent crease while maintaining comfort is desirable in textile products. Traditionally, fabrics are impregnated with resin to impart wrinkle resistance to textiles. However, this approach decreases tensile strength of the fiber, abrasion resistance, and dyeability while inducing hydrophobicity. To impart wrinkle resistance, NPs have been applied to cotton and silk. TiO_2 NPs with carboxylic acid as a catalyst were utilized to form cross-links between cellulose molecules and the acidic groups.^{40,41} The use of 1,2,3,4-butane tetracarboxylic acid (BTCA) and succinic acid as cross-linking agents had the highest dry crease recovery angle and wet crease recover angles, respectively. Additionally, carboxylic-acid-treated fabrics with TiO_2 NPs were softer compared to untreated fabric.⁴¹ TiO_2 through its catalytic property can be used as a cocatalyst with sodium hypophosphite (NaPO_2H_2) to treat cotton with 1,2,3,4-BCTA.^{25,42–44} Figure 2c shows SEM images of cotton fibers treated with BTCA and TiO_2 NPs. This increased the effectiveness of NaPO_2H_2 , hence the wrinkle recovery of the cotton fabric. However, tear and tensile strength of the cotton fabric decreased due to the presence of TiO_2 NPs. *Bombyx mori* silk was also treated with TiO_2 NPs in chitosan by cross-linking reactions of citric acid and maleic anhydride.⁴⁵ Dry and wet delay-wrinkle recovery angles of the treated silk were 267 and 250° compared to untreated fabric of 235° and 178°, respectively. Additionally, SiO_2 NPs and maleic anhydride as a catalyst have been applied to silk to improve wrinkle resistance.⁴⁶

Strength Enhancement. CNT-reinforced polymer composite fibers have been developed to improve strength and toughness and to decrease weight. These composite fibers could be produced through melt-spinning of polypropylene and carbon particles.⁴⁷ Controlling the parameters in melt-spinning, the morphology, crystallinity, and mechanical properties of nanostructured polycaprolactone nonwoven mats were optimized.⁴⁸ Melt extrusion also produced a wide range of nanoadditive yarns with improved mechanical properties and various textures.⁴⁹

Wet–dry spinning or jet melt-spinning through spinnerets have been used to produce ordinary and fine denier textile fibers (1–100 μm in diameter). Nanoscale fibers require electrospinning, in which a solution is extruded through nanoscale spinnerets and the spun fibers are collected on a grounded plate. The fiber strength and conductivity can be increased by post-treatment approaches (e.g., heat). Synthetic nanofibers can also be produced through coagulation-based CNT electrospinning by controlling the fiber diameter and increasing twist. Such composite fibers can consist of multiwalled CNTs (5–20). Highly twisted yarns have high strength, toughness, and energy damping capability for application in electronic textiles including actuators, electrostatic discharge protection, energy storage, heating, and radio

and microwave absorption. The integration of CNTs into fibers has been shown to improve the strength and performance. For example, superaligned arrays of CNTs have a Young's modulus in the TPa scale, tensile strength of 200 GPa, breaking strain of 20%, and elastic stain of 5%.⁵⁰

Dipping and coating method was also utilized to immobilize CNTs on cotton.²⁶ CNTs were modified with poly(butyl acrylate) using surface grafting, and this composite was applied to cotton fabrics by dipping, drying, curing, and finishing. Figure 2d illustrates SEM images of CNT-coated cotton fibers. The tensile strength of the CNT-coated cotton fabrics was improved along the weft and warp directions, showing enhancement in both loading capability and flexibility (displacement). For example, the tensile strength of the CNT-coated cotton was 0.5 kN at 13.5 cm displacement as compared to 0.25 kN for untreated fabrics.²⁶

UV Blocking. Inorganic UV blockers are nontoxic and chemically stable, operating at high temperatures. Nanoscale semiconductor oxides such as TiO_2 and ZnO efficiently absorb and scatter UV radiation.^{51–54} At the nanoscale, scattering depends on the wavelength and the size of the NP, where the scattering is inversely proportional to the wavelength of the fourth power of the wavelength. For example, to scatter UV light (200–400 nm), the optimum particle size is 20–40 nm.⁵⁵ Sol–gel method can be used to form a thin layer of TiO_2 on the surface of the treated cotton. The UV protection effect may be maintained up to 50 launderings.⁵⁶ Furthermore, ZnO nanorods (10–50 nm) have been incorporated in cotton to induce scattering at a high UV protective factor rating.⁵⁷ Figure 2e shows a SEM image of ZnO nanorods grown on cotton fibers.²⁷ Additionally, ZnO NPs synthesized through sedimentation and peptization were immobilized on dyed polyester/cotton fabrics.^{58,59} The resulting fabric absorbed the light in the UV region.⁵⁸

Antibacterial Properties. Ag, TiO_2 , and ZnO NPs can be utilized to impart antibacterial and fungicidal properties to textiles.^{53,55,60–62} Ag NPs have large surface areas that increase their contact with bacteria and fungi. The antiseptic mechanism of Ag NPs is based on reacting with proteins in these organisms and adversely affecting their cellular function and inhibiting cell growth. They also reduce respiration, limiting the activity of the basal metabolism of the electron transfer system, and substrate transport into the cell membrane. When Ag NPs contact with moisture or bacteria, they adhere to the cell wall and membrane.⁶³ While the Ag NPs in their metallic state are inert, they ionize in the presence of moisture. The Ag^+ ions are reactive, and they diffuse through the cell wall and membrane into the cytoplasm. Ag^+ ions bind to sulfur-containing proteins on the cell membrane to structurally change the cell wall.⁶⁴ These structural changes result in the release of the cellular components to extracellular fluid due to the changes in the osmotic pressure. Additionally, the Ag^+ ions bind to phosphate-containing proteins to condense DNA, leading to a reaction with thiol group proteins to cause cell death. They also suppress the function of enzymes and inhibit the cell to produce ATP.⁶⁵ Ag NPs slow the growth and multiplication of bacteria and fungi that are involved in odor creation and itchiness. Figure 2f shows cotton fibers treated with Ag NPs.²⁸ For example, Ag NPs can be applied to socks to prevent the growth of bacteria and fungi.

The antimicrobial efficacy of Ag additives depends on the concentration, surface area, and the release rate of the Ag^+ ions.^{66–68} Ag-containing textiles can release dissolved and

particulate Ag (20–30%) into washing liquid in the first cycle.^{69–71} In fabrics comprising Ag metal, oxidation from Ag(0) to Ag(I) is required for releasing Ag⁺ ions in solution.⁷⁰ Ion release from Ag NPs is a cooperative oxidation process involving dissolved oxygen and protons to produce peroxide intermediates and complete reactive dissolution. The presence of oxygen is essential for the release of dissolved Ag through the surface oxidation of Ag NPs. The ion release rates increase as the temperature is increased and as the pH is decreased.⁷² For example, Ag NPs (2 mg L⁻¹) released 0.3 mg L⁻¹ dissolved Ag after 24 h incubation in air-saturated solution (9.1 mg L⁻¹ dissolved oxygen) at pH 5.68. The release of dissolved Ag was 0.6 and 0.1 mg L⁻¹ at pH 4.0 and 8.0 after 24 h incubation, respectively.⁷² Additionally, the change in ionic strength has a negligible effect on the release kinetics.

TiO₂ NPs can also be utilized to impart textiles with antibacterial properties. Upon illumination with light with energy higher than its band gap (3.2 eV), TiO₂ as a photocatalyst has the ability to have its electrons jump from the valence band to the conduction band. The electron and electric hole pairs form on the surface of the photocatalyst, where the electrons and oxygen form O₂⁻ and the positive electric holes and water create hydroxyl radicals.⁵² The unstable substances on the surface of the photocatalyst are oxidized into CO₂ and water. Through this mechanism, the photocatalysts decompose organic matter including odor molecules, bacteria, and viruses. The catalytic activity of TiO₂ NPs has been utilized in textiles to provide antibacterial properties.^{56,73} The photocatalytic activity might be improved by creating TiO₂/SiO₂ nanocomposites or Au-doped TiO₂ nanocomposites in cotton fabrics with self-cleaning properties.^{74,75} Furthermore, ZnO behaves similar to TiO₂ to produce antibacterial properties.⁷⁶ ZnO NPs (21–25 nm) have been synthesized in reverse micelle cores of polystyrene (PS) and poly(acrylic acid).⁷⁷ ZnO NPs coated onto textiles showed self-cleaning properties in the presence of Gram-negative *Escherichia coli* and aerobic Gram-positive *Staphylococcus aureus*. Additionally, SiO₂ and Ag NPs with core–corona structure were electrostatically assembled onto cotton surfaces with high packing density to impart antibacterial properties to fabrics.⁷⁸ The coronas of NPs can be loaded with antibacterial moieties such as quaternary ammonia salts as well as metal coatings on cotton fabrics.⁷⁹ Discussions focusing on self-cleaning and antimicrobial nanomaterials in textiles can be found elsewhere.^{16,80,81}

ELECTRONICS IN TEXTILES

Electrical Conductivity. Conducting polymers are attractive for creating textiles that enable the incorporation of sensors and actuators. For example, conducting polymers can change their resistivity and produce electrical signals in response to external stimuli. A range of dopants can be incorporated in these polymers. For example, polypyrrole (PPy) has high mechanical strength and is electroactive in organic and aqueous solutions. Another widely studied conductive polymer is polyaniline (PANI), which exists in three possible configurations: leucoemeraldine base (fully reduced), emeraldine base (partly oxidized), and pernigraniline base (fully oxidized). In its oxidized form, the conductivity of PANI increases about 10 orders of magnitude. Additionally, polythiophene (PT) and its derivatives can be in p- or n-type forms for application in field-effect transistors in flexible logic circuits. The low production costs, light weight, and flexibility allow these materials to be easily integrated in textiles.

The surface structure of synthetic fibers can be modified to produce diverse functionalities.⁸² SiO₂ NPs can be incorporated in polyimidoamide fibers through spinning. Incorporation of NPs in PAN fibers can create electrically conductive channels with enhanced mechanical and antistatic properties.^{39,83} Fiber porosity and thermal and absorption characteristics can be controlled by chemically modifying the fibers. To improve thermal resistance and tenacity, the fibers can be coated with diamine (diaminodiphenylmethane), montmorillonite, and SiO₂ NPs.^{84–86} Synthetic fibers can also be functionalized through chemical oxidative deposition, in which conducting electroactive polymers such as PANI, PPy, and PTs are used to coat textiles for improving tensile strength and thermal stability.^{87,88} Furthermore, surface deposition of electroactive polymers increases conductivity of the fibers 1 order of magnitude.^{89–91} Such composite fibers have application in the reduction of static electrical charge, microwave attenuation, and electromagnetic shielding.

Finding the balance between electrical conductivity, flexibility, and comfort of the textile is a challenge. Coatings have been developed to impart electrical conductivity to cotton. One approach involved polyelectrolyte-based coating with multi-walled carbon nanotubes (MWCNTs).⁹² Figure 3a shows SEM images of MWCNT–Nafion-coated cotton threads. Charge transport through the network of nanotubes was 20 Ω cm⁻¹. Another strategy used a combination of metal NPs conformally coated around the heterogeneous contour of cotton fibers.⁹³ In

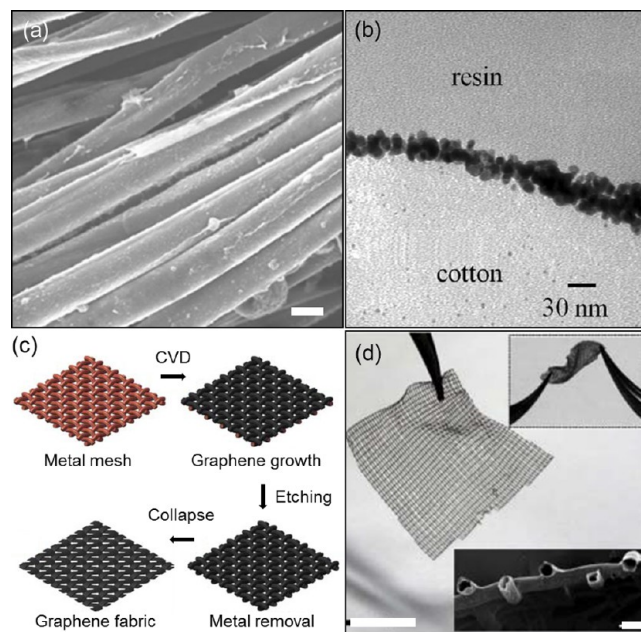


Figure 3. Conductive nanomaterials in textiles. (a) SEM image of MWCNT–Nafion-coated thread. Scale bar = 10 μm. Reprinted from ref 92. Copyright 2008 American Chemical Society. (b) TEM image of a cross section of the conductive Au NP and PEDOT-coated cotton fibers. Reprinted with permission from ref 93. Copyright 2011 Elsevier. (c) Fabrication of graphene woven fabric by CVD using copper (Cu) wire meshes as substrates. Reprinted with permission from ref 94. Copyright 2012 Nature Publishing Group. (d) Graphene woven fabric in PDMS. Scale bar = 5 mm. The top inset illustrates the twisted graphene fabric film. The bottom inset shows an SEM image of a graphene fabric cross section. Scale bar = 100 μm. Reprinted with permission from ref 94. Copyright 2012 Nature Publishing Group.

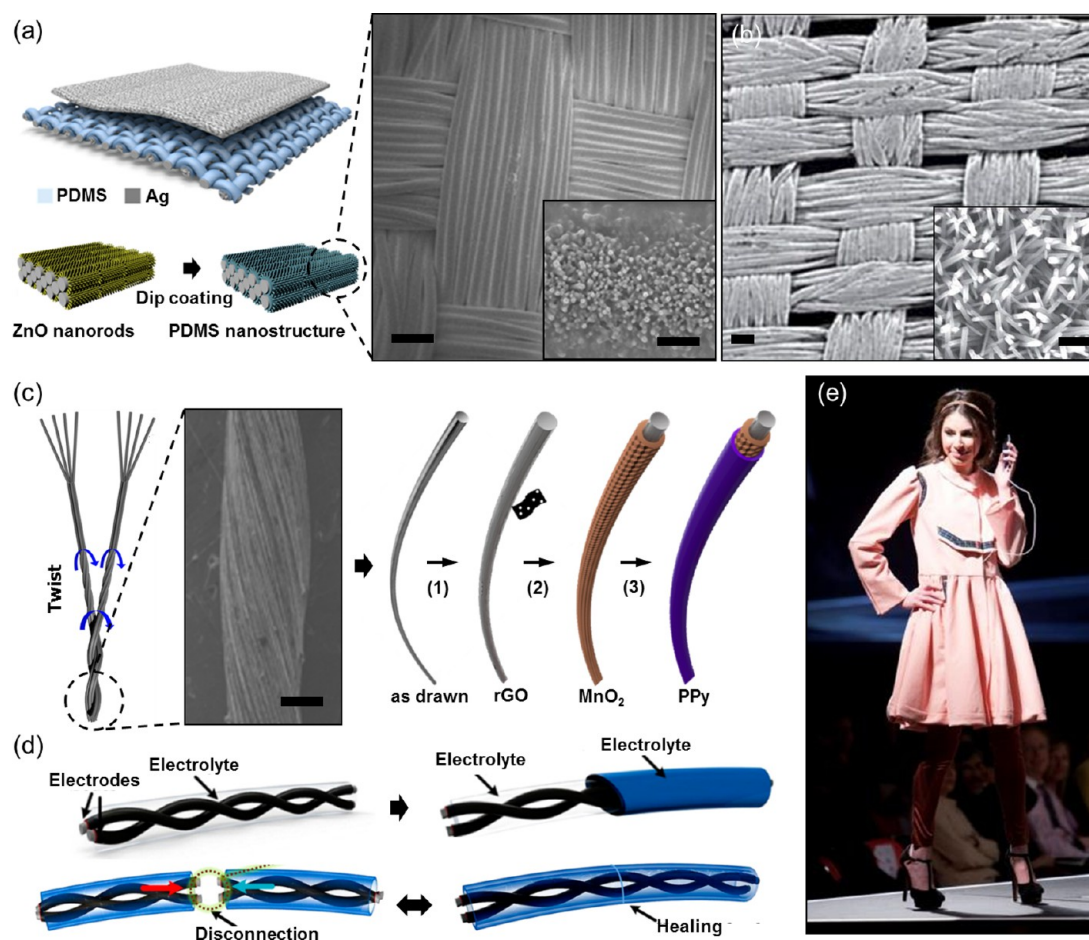


Figure 4. Energy generation and storage in textiles. (a) Fabrication of a nanopatterned wearable triboelectric nanogenerator showing SEM images of ZnO nanorod-templated PDMS nanopatterns. The inset shows a magnified image of surface morphology. Scale bar = 500 μm ; inset scale bar = 1 μm . Reprinted from ref 99. Copyright 2015 American Chemical Society. (b) SEM images of a textile electrostatic-piezoelectric hybrid nanogenerator containing ZnO nanowires. The inset shows magnified nanowires on the surface. Scale bar = 500 μm ; inset scale bar = 1 μm . Reprinted with permission from ref 101. Copyright 2012 The Royal Society of Chemistry. (c) Twisted yarn fabrication and illustration of the yarn functionalized by rGO, MnO₂, and PPy. (1) Hydrothermal treatment; (2,3) electrodeposition. Reprinted from ref 102. Copyright 2015 American Chemical Society. (d) Fabrication and operation principle of magnetic-assisted, self-healable, yarn-based supercapacitors. Reprinted from ref 103. Copyright 2015 American Chemical Society. (e) Garment using cotton yarns coated with nanolayers of PEDOT-PSS. Copyright Abbey Liebman.

situ polymerization was utilized to create polymeric bridges between the NPs. These flexible bridges allowed for the creation of coatings that were durable and resilient to mechanical deformation for application in cotton-based transistors. Figure 3b shows a transmission electron microscope (TEM) image of a cross section of the conductive cotton fibers, showing uniform coating with Au NPs and poly(3,4-ethylenedioxythiophene) (PEDOT).

Graphene-based woven fabrics have been prepared by interlacing two sets of graphene microribbons.⁹⁴ The resulting textile had dimensional stability in both the warp and the weft directions. The conductivity was optimized by tuning the ribbon packing density. Graphene woven fabrics were synthesized through atmospheric chemical vapor deposition (CVD) using Cu meshes consisting of wires with $\sim 60\ \mu\text{m}$ in diameter as substrates. The fabrication of the textiles involved growing graphene on the substrate, removing the Cu mesh wires, and subsequently collapsing the graphene to form double-layer microribbons (Figure 3c). Such polymers could be also embedded in PDMS or PET films (Figure 3d). The constructed fabric had 90% light transmission (550 nm) at

1000 $\Omega\ \text{sq}^{-1}$.⁹⁴ Conductive textiles could also be produced by immobilizing graphene *via* reduction from graphene oxide on cotton fabric by using a conventional dip and dry method.⁹⁵ The electrical conductivity of the fabric enhanced 3 orders of magnitude as the number of coating cycles was increased from 1 to 20. The surface conductivity of the resulting graphene depended on the reducing agent type and concentration. The electrical resistivity of the graphene-immobilized cotton ranged from 10^3 to $10^6\ \text{k}\Omega\ \text{cm}^{-1}$.⁹⁵

Power Sources. Flexible and lightweight fabric supercapacitor electrodes have been designed for energy storage.⁹⁶ Activated carbon in poly(methyl methacrylate) (PMMA) and polyethylene glycol (PEG) was incorporated in woven cotton and polyester fabrics. The supercapacitor cells were assembled in a conventional symmetrical two-electrode setup by screen printing on polyester microfibers. Electrodes coated with activated carbon had a gravimetric and areal capacitance of 85 F g^{-1} at 0.25 A g^{-1} on a cotton lawn and polyester microfiber.⁹⁶ Recently, a flexible supercapacitor textile consisting of a CNT/PANI composite fiber was developed.⁹⁷ The supercapacitor was integrated with a photoelectric conversion

function to create a self-powering energy textile that converted solar energy into electrical energy and stored it in a stacked multilayer structure. The CNT array was synthesized by CVD. Aligned CNT sheets were dry-drawn from the array and stacked into a thicker film along the length direction and twisted into an aligned fiber, which was woven into textiles. The resulting textiles were electrodeposited with PANI to create an electrode, followed by coating with a layer of gel electrolyte to create a supercapacitor. The resulting material had a capacitance of 272 F g^{-1} with 96% maintenance after 200 bending cycles.⁹⁷ Another study that aimed to improve the performance of textile-based supercapacitors involved embedding a metal wire (monofilament) in the center of a CNT yarn.⁹⁸ One-step continuous spinning allowed formation of a core/sheath-structured CNT yarn architecture to create linear supercapacitors. CNTs formed a layer around the conductive metal filament core. The filament core acted as a current collector to transport charges. Foldable nanopatterned wearable triboelectric nanogenerators were also reported.⁹⁹ Figure 4a shows the device and its fabrication process using a nanopatterned PDMS structure. Ag-coated textile and PDMS nanopatterns based on ZnO nanorod arrays were used as triboelectric materials. The nanopatterned structures produced 120 V (output) at $65 \mu\text{A}$, and four-layered triboelectric nanogenerators produced 170 V (output) at $120 \mu\text{A}$. No significant drift was observed after 120 000 cycles.⁹⁹ Another study reported the development of carbon-activated cotton threads on textile for energy generation.¹⁰⁰ The device harvested electrostatic energy from the environment through contact and friction electrifications. It was fabricated by treating carbon black NPs and encapsulating them with a thin layer of PDMS for stability. By rubbing and tapping with a PTFE sheet, electrostatic charges were collected from the carbon-functionalized threads in textiles. The device had an open-circuit voltage of -60.9 V .¹⁰⁰ Piezoelectricity *via* electrostatic forces was also utilized in textiles to create a nanogenerator.¹⁰¹ ZnO nanowires and discharge films were incorporated into a textile to hybridize electrostatic and piezoelectric effects (Figure 4b). This nanogenerator had an output voltage of 8 V at $2.5 \mu\text{A}$. The produced power source was utilized to power an OLED and a liquid crystal display (LCD) panel.¹⁰¹ Recently, pristine soft conductive yarns were produced *via* a twist-bundle-drawing technique (Figure 4c).¹⁰² Conductive yarns modified with reduced graphene oxide (rGO), MnO_2 nanosheets, and PPy films were used to produce weavable supercapacitors. The yarns had specific capacitances of 31 and 411 mF cm^{-1} in solid-state two-electrode cells with energy densities of $9.2 \mu\text{Wh cm}^{-2}$ and 1.1 mWh cm^{-3} .¹⁰²

Stretchable PPy-based supercapacitors with cycling stability were also fabricated.¹⁰⁴ Electrochemical deposition of PPy on stretchable stainless steel meshes allowed solid-state supercapacitors to be produced, reaching 170 F g^{-1} at 0.5 A g^{-1} . Under 20% strain, the capacitance can be enhanced up to 214 F g^{-1} . These supercapacitors were operated at a scan rate of 10 V s^{-1} , which is a magnitude higher than PPy electrodes in aqueous solutions. These solid-state supercapacitors under no strain and 20% strain had capacitance retentions of 98 and 87% at 10 A g^{-1} after 10 000 cycles.¹⁰⁴

In conventional planes or structures, the reconnection of the broken yarn electrode and the restoration of the electrical conductivity are challenging.¹⁰³ To improve the mechanical properties, yarn-based supercapacitors with self-healing properties have been developed. The electrodes were fabricated by

wrapping magnetic electrodes around a self-healing polymer shell (Figure 4d). The magnetic attraction reconnected broken fibers in the yarn electrodes to store electrical conductivity, while the polymer shell recovered mechanical strength and configuration integrity. The magnetic yarns allowed the specific capacitance to be restored up to 71.8% after four breaking cycles by maintaining mechanical properties.¹⁰³

Conductive fabrics have been incorporated in garments. Figure 4e shows a garment using cotton yarns coated with nanolayers of PEDOT–poly(styrenesulfonate) (PSS) deposited over an array of Au NPs. These nanolayers allowed the cotton yarns to become electrically conductive and transfer energy from solar cells attached to the exterior of the dress. A discussion about energy storage technologies can be found elsewhere.⁹

Fabrication of multifunctional composite fibers has received attention due to their applications in conductive structures and batteries in the textile industry. Here, “fiber” refers to wire-like composite structures produced *via* drawing techniques used in the production of fiber optics. Composite fibers can be fabricated through preform heating and drawing. A geometrically complex fiber preforms at a length of tens of centimeters and is assembled by stacking of tubes, rods, multilayered films, or functional components within a hollow rod that serves as cladding.¹⁰⁵ The preform tip is then placed into the vertical furnace, where the temperature is increased above the softening or melting temperature of the preform materials. As a consequence, the preform tip melts, and then it is pulled downward, thus creating a slender rod that can be continuously pulled from the molten preform tip. Typically, a clamp tractor or a spooler is used to pull the fiber at a constant speed and tension. Geometry of the resultant fiber depends on parameters in the drawing process such as temperature distribution in a furnace, fiber drawing speed and preform feed velocity, pressurization of the preform, and electromagnetic fields.¹⁰⁶ This process creates both non-optical fiber and optical fibers. Fibers drawn from the macroscopic preform would generally retain the preform structure; however, sizes of the constituent structures (*e.g.*, layers, rods) will be reduced to micro- or nanoscale. Therefore, a geometrically complex, composite transverse structure could be realized within a fiber on a submicron scale by controlling the preform structure and optimizing the conditions of the fiber drawing process. This, generally, may not be accomplished by traditional yarn-spinning methods such as melt-spinning,¹⁰⁷ wet-spinning,¹⁰⁸ or electrospinning,^{109,110} which are typically utilized to produce fibers and yarns with simple structures in textile manufacturing. Moreover, materials including biofunctional polymers,^{111–113} low-melting-temperature metal alloys,¹¹⁴ optical plastics,^{114–123} conductive polymers,^{124–126} and electrochemical materials^{127–129} could be integrated into a composite fiber during drawing.

Flexible fiber or stripe batteries which can be directly weaved into a textile constitute a promising solution toward seamless integration with functional textiles. Flexible fiber batteries using both a simple inorganic chemistry^{127,128} as well as Li-ion chemistry¹²⁹ have been proposed. The simplest fiber battery consisted of a microstructured low-density polyethylene (LDPE) jacket with several intercommunicating channels running along the fiber. Aluminum (Al) and Cu wires were immobilized to produce a double-stranded fiber as anode and cathode, respectively. The voids between these two channels were then filled with sodium hypochlorite (NaOCl) electrolyte.

This fiber constituted a typical Al/air galvanic cell. To fabricate a fiber battery, the fiber jacket preform was prepared by drilling several interconnected channels throughout a LDPE rod. The two electrode wires (Al and Cu) were embedded into the two extreme channels of the fiber during production (*i.e.*, drawing). Open cell voltage of a fiber battery was ~ 1.5 V with a linear capacity of 10^{-2} – 10^{-1} mAh cm $^{-1}$. Flexible Li-ion batteries could be built by from poly(ethylene oxide) (PEO) as a thermoelastic polymer ionic electrolyte in all the electrodes and a separator layer. To assemble such a battery, a solvent-casting method could be used to deposit an anode layer ($\text{Li}_4\text{Tl}_5\text{O}_{12}$ + PEO), a separator layer (PEO + LiI), and a cathode layer (LiFePO_4 + PEO) in sequence. The thermoelastic nature of PEO allows the production of such batteries in fiber drawing. This Li-ion battery could be cut into stripes that might be directly weaved into a textile.

Two prototypes of textiles based on fiber and stripe batteries have been demonstrated. The first prototype was fabricated by weaving fiber batteries into a wool textile matrix.¹²⁷ The maximum output power of a fiber battery textile could be achieved by optimizing series and parallel connections of the fiber batteries in the textile. Applications of this fiber-battery-integrated textile included lighting up a LED, driving a wireless mouse,¹²⁷ and actuating a shape-memory alloy.¹²⁷ The second prototype used flexible stripe Li-ion batteries.¹²⁹ The Li-ion battery stripes were weaved into a textile. Each stripe had an open cell voltage of ~ 0.3 V. A textile battery made of eight battery stripes woven with wool threads and connected in series using Cu and Al wires were used to light up a 3 V LED. The flexible fiber or stripe batteries constitute a promising technique toward the realization of on-garment power supply. In the fashion industry, LEDs or electroluminescent wires are used as light-emitting elements, and shape-memory alloys may be weaved into garments to provide kinetic features. The fiber and stripe batteries could be used as an efficient power source for these electronics.

Conductive fibers are widely used to interface with other electronic devices integrated into textiles. To fabricate conductive fibers, conductive fillers such as carbon black (CB)¹²⁵ or CNTs¹³⁰ are impregnated into plastic preform material. Fabrication of all-fiber electronic components is, however, a challenging task. The fabrication of a fiber electric capacitor using CB-impregnated LDPE films as compliant electrodes has been reported.^{124–126} The fiber preform was fabricated by consecutive stacking of two conductive and two isolating LDPE layers and then turning the multilayer into a Swiss-roll configuration featuring a large central hole. A tension-adjustable reel was installed on the top of the fiber drawing tower that hosted a spool of Cu wires. These wires were then passed through the preform core, pulled down, and embedded into the fiber center during drawing by collapsing the plastic cladding. The as-drawn fiber capacitors featured one or two Cu wires as inner electrodes, and the outermost conductive LDPE layer constituted the outer electrode. The fiber capacitance was measured in the 60–100 nF m $^{-1}$ range. The fiber capacitors were also demonstrated to build touch-sensitive textiles.

Digital Components. OLEDs have been incorporated in soft fabrics.¹³¹ OLEDs fabricated by thermal evaporation were mechanically stable over a 1000 cycle bending test with a bending radius of 5 mm, an emission angle of 70°, and a current efficiency of ~ 8 cd A $^{-1}$.¹³¹ Schottky diodes were also fabricated on textiles.¹³² ZnO nanorods were grown on a Ag-coated textile

fabric using a hydrothermal method, and Zn nitrate and hexamethylenetetramine were used to produce ZnO nanorods. The Schottky diode was prepared by applying a photoresist and reactive plasma ion etching of the ZnO nanorods. A shadow mask was used to deposit Cu using thermal evaporation. The resulting diodes had a performance comparable to that of glass-based diodes.¹³² Schottky diode integrated textiles have potential applications in switched-mode power supplies, voltage clamping, and reverse current and discharge protection.

Polymer yarns/fibers that are twisted/embedded with metal wires have been used for production of electromagnetic shield garments and fabrics. These metal wires could be embedded into polymer rods during a drawing process. The metal components in such rods generally have a melting temperature similar to that of polymers. A polycarbonate cable containing arrays of the bismuth–tin ($\text{Bi}_{42}\text{Sn}_{58}$, melting temperature ~ 140 °C) micro/nanowires has been fabricated using the stack-and-draw technique.¹¹⁴ A molten $\text{Bi}_{42}\text{Sn}_{58}$ alloy was first filled into a polycarbonate tube to produce a preform that was subsequently drawn into the cable. The resulting cable had a cross section featuring a metal core surrounded by a polycarbonate cladding. By stacking these cables within another polycarbonate tube and by repeating the drawing process, metal wire arrays could be produced at smaller dimensions. After several drawings, nanowires separated into NPs. Recently, the fabrication of polymer/wire composites containing indium^{133,134} or tin–zinc^{135–143} has been demonstrated based on the same drawing technique. While such polymer/metal wire composites are mainly used for electromagnetic shielding, they also have a potential for producing metamaterials and optical components.

PHOTONIC TECHNOLOGIES FOR TEXTILES

Integration of optical technologies into garments and apparel is desirable in the fashion industry. Photonic materials and devices including films, nanoadditives, or optical fibers have been adopted in the fabrication of textiles and garments to not only enhance the aesthetic performance but also endow the garments with additional functionalities. The most distinctive and basic application of optical technologies on fabrics or garments is perhaps tuning their appearance by controlling the intensity, color, and pattern of light. For example, optical films made of periodical dielectric multilayers could be directly coated on fabrics, thus offering a highly reflective colorful appearance and enabling different color perceptions depending on the angle of observation. Holographic films may also achieve similar functions and even provide a more complex 3D visual effect.^{144,145} Additionally, phosphorescent films can allow fabrics to glow in the dark.¹⁴⁶ Optical additives such as thermochromic and photochromic inks could be applied to yarns or textile, thus enabling the change of a textile color in response to ambient heat or illumination.¹⁴⁷ Retro-reflective inks that could provide a high reflection directly toward a light source are widely used for security clothing.¹⁴⁴ Moreover, electroluminescent wires or optical fibers serving as light-emitting elements could be seamlessly weaved into a textile or garment. Textiles based on electroluminescent wires,^{148,149} traditional single- or multimode optical fibers,¹⁵⁰ fluorescent fibers,¹⁵¹ and photonic band gap fibers¹⁵² have been demonstrated. In addition to promoting aesthetics, multifunctional fibers could offer textiles with functionalities such as sensing of temperature,^{153,154} humidity,¹⁵⁵ strain,¹⁵⁶ bending,¹⁵⁷ and pressure,¹⁵⁸ optical displays,¹⁵⁹ data transfer and communication,¹⁶⁰ lasing,¹⁶¹ and illumination.^{159,162}

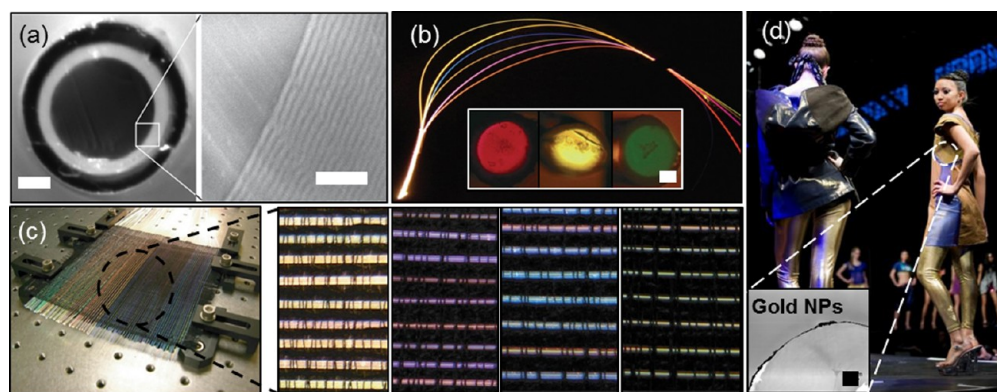


Figure 5. Fiber-optic and plasmonic technologies for textiles. (a) Cross section of a solid-core Bragg fiber and its multilayer structure. Scale bar = 50 μm ; inset scale bar = 10 μm . Reprinted with permission from ref 116. Copyright 2008 The Optical Society of America. (b) Light scattered from solid-core Bragg fibers. The inset shows Bragg fibers with different band gaps. Scale bar = 200 μm . Reprinted with permission from ref 116. Copyright 2008 The Optical Society of America. (c) PBG Bragg fibers woven into a black silk textile. The inset shows the color of the fibers tuned by mixing the emitted guided color with the diffracted color from ambient illumination. Reprinted with permission from ref 116. Copyright 2008 The Optical Society of America. (d) Use of plasmonic NPs in a garment. The inset shows an SEM image of Au NPs on the surface of a cotton fiber. Scale bar = 500 nm. Reprinted from ref 165. Copyright 2009 American Chemical Society. Reprinted with permission from Olivia Ong.

Color-Tunable Optical Fibers. Bragg fibers, a subset of photonic band gap fibers, have a hollow or solid core surrounded by periodic dielectric nanolayers with high- and low-refractive indexes (Figure 5a).^{115–120} Recently, two methodologies have been reported for the fabrication of the all-polymer hollow-core Bragg fiber preforms.¹²³ One approach utilized consecutive deposition of layers of two different polymers by solvent evaporation inside a rotating polymer cladding tube. The other approach adopted co-rolling of two different polymer films inside a plastic tube. Solid-core Bragg fiber preforms were fabricated by co-rolling the multilayer around a rod.^{154,155,157,158} To fabricate Bragg reflectors, PMMA/PS or PVDF (polyvinylidene fluoride)/polycarbonate have been used. Solid-core Bragg fibers were manufactured by preform heating and drawing, while hollow-core fibers required core pressurization. Bragg fibers typically guide the light by the band gap effect.¹⁶³ Band gaps of Bragg fibers are defined as spectral regions of high diffraction efficiency caused by the interference effects inside a periodic multilayer. Upon launching spectrally broadband light into a Bragg fiber, only the spectral components within the reflector band gaps would be strongly confined and thus guided in the optical fiber core (Figure 5b). For the wavelengths outside the reflector band gap, the light penetrated deeply into the multilayer region exhibits high propagation loss due to scattering from the imperfections inside the multilayer structure. Therefore, narrow-band colors were observed at the output end of a Bragg fiber (Figure 5b inset). Spectral position of the band gap was affected by the core refractive index and multilayer geometry. Thus, a band gap guidance mechanism renders Bragg fibers suitable for application in spectral filtering,^{118,119} optical sensing,^{117,119–121,164} and photonic textiles.^{116,122,152}

The key feature of band gap guidance of a Bragg fiber is wavelength filtering. When launching broadband light into a Bragg fiber, only a specific color defined by the spectral position of the reflector band gaps is guided. All the other colors are scattered out of the fiber after several centimeters of propagation. Moreover, due to the finite number of multilayers in the Bragg reflector, guided light partially leaks out from the fiber core. The leakage rate could be controlled by changing the

number of multilayers. The spectral position of the reflector band gaps, and hence the guided color, could be varied by changing the thicknesses of the reflector layers, with thicker layers shifting band gaps to longer wavelengths. Layer thicknesses have been varied by drawing geometrically similar preforms to optical fibers of different diameters.^{116,122,152} Furthermore, under ambient (external) illumination, the Bragg fibers are colored depending on their diffraction properties. Therefore, the fiber color under ambient illumination is typically different from the fiber color due to emission of the guided light. This offers an opportunity to tune the overall fiber color by controlling the relative intensities of the ambient and propagating light. A ribbon of Bragg fiber diffracted green under ambient illumination, while an emission of guided light diffracted red. In the far field (defocused view), the resultant color of a fiber ribbon was yellow.^{116,122}

Photonic Textiles Based on Bragg Fibers. A photonic textile based on solid-core Bragg fibers was hand woven on a Dobby loom.¹¹⁶ The photonic textile showed colors when externally illuminated (Figure 5c). The textile exhibited colored bands made of optical fibers with similar diameters and coloration. Upon launching broadband light, the textile sample showed a number of brightly lit bands of distinct colors. The inset of Figure 6c shows textile samples under the ambient illumination. The textile sample had different colors depending on whether the textile was lit or not. This opens the possibility of controlling the resultant textile color by balancing the intensities of the guided and ambient light. When used in the fashion industry, Bragg fibers and photonic textiles based on these optical fibers could be conveniently weaved into garments. Compared to yarns or fabrics decorated by optical coatings or pigments, Bragg fiber-based textiles are resistant to mechanical abrasion and would not fade in color even under repeated washing.

Plasmonic Textiles. Cotton fabrics were also colored using arrays of plasmonic Ag, Au, and Ru NPs.¹⁶⁵ The color in the fabrics originates from the close packing of NPs, which were displayed on a garment (Figure 5d). TEM micrographs of the cotton fibers show the presence of conformal coatings of NPs

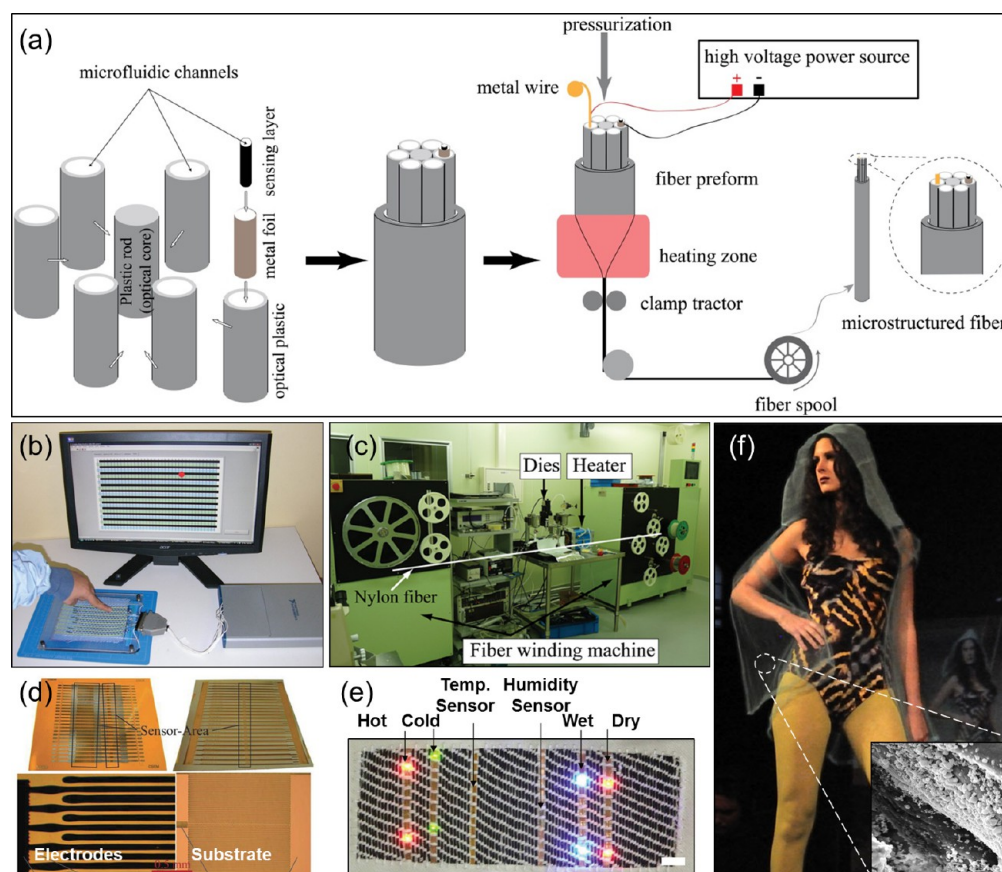


Figure 6. Sensors and insecticide-releasing textiles. (a) Fabrication of multifunctional fiber composites for sensing applications. (b) Woven touchpad sensor with a 1D array of capacitor fibers connected to the ADC board to monitor an image of a textile with a reconstructed touch position. Reprinted with permission from ref 124. Copyright 2012 IOP Publishing. (c) Dye-coating system used in forming PEDOT:PSS and Cytop film on fibers. Reprinted with permission from ref 172. Copyright 2012 Elsevier. (d) Fabrication of electrodes *via* photolithography for sensing applications. Reprinted with permission from ref 173. Copyright 2013 IEEE. (e) Temperature and humidity sensors woven in a tablecloth. Scale bar = 1 cm. Reprinted with permission from ref 174. Copyright 2010 Wiley-VCH Verlag GmbH & Co. KGaA. (f) Permethrin-releasing textile net. Reprinted with permission from ref 175. Copyright 2012 Springer. Reprinted with permission from Matilda Ceesay.

assembled on the perimeters of the cotton fibers (Figure 5d, inset).

SENSING AND DRUG RELEASE IN TEXTILES

Plasmonic optical fiber sensors can be fabricated *via* drawing techniques. Plasmonic sensors have been studied due to their high sensitivities for bio/chemical sensing.^{166–168} In a plasmonic fiber sensor, a lossy surface plasmon mode propagating along a metal/dielectric interface can be excited at its resonance by an optical fiber core-guided mode *via* evanescent wave coupling when the phase-matching condition between the two modes is satisfied at a certain frequency. The presence of such a plasmonic mode manifests itself as a spectral dip in the fiber transmission spectrum, with its spectral location corresponding to the phase-matching frequency. Variations in the refractive index of an analyte adjacent to the metal layer could significantly modify the phase-matching condition, thus displacing the spectral dip in the optical fiber transmission spectrum. This constitutes the general sensing principle of a plasmonic fiber sensor. In the fabrication of a plasmonic sensor using conventional single- or multimode optic fibers, a series of modifications such as cladding etching or polishing followed by a subsequent deposition of several tens of metal nanolayers are generally required, in addition to the interfacing with a microfluidic system in the proximity of the fiber-sensing

head.^{169–171} These procedures bring challenges to the development of plasmonic fiber sensors. However, a complete plasmonic sensor fiber can be fabricated using stack-and-draw technique (Figure 6a). A fiber preform is first assembled at the microscale, and it contains a plastic fiber core rod surrounded by the plastic tubes, with one of them hosting a low melting temperature metal foil functionalized with a thermoplastic sensing layer. The inner channel of that tube is later used as a channel for analyte delivery. Next, the preform assembly is drawn into the fiber under pressure to keep the microfluidic channels in the fiber open. Finally, an additional wire can be passed through one of the tubes during drawing and later used for active temperature control of the device. Additionally, a high-voltage supply can be connected to the wire and a foil to tune the distance between the fiber-optic core and the plasmonic layer during drawing. Such fibers may contain multiscale features ranging from nano- to macroscale and consist of nanoadditives for functionalization.

Using flexible fiber capacitors, touch sensor fabrics have been developed.^{124,125} Flexible and elastic fiber capacitors are well-suited for a conventional weaving process. A Dobby loom was used to weave the capacitor fibers into a 1D sensor array integrated into a wool textile matrix. The touch sensor fabric consisted of 15 capacitor fibers (Figure 6b). The inner electrodes of all the fibers (Cu wires) were connected to the

voltage source integrated into an analog-to-digital converter (ADC) card. One end of the outer plastic electrode of each fiber was grounded, while the other end was connected to the individual channels of the ADC card to measure the voltage at the fiber end point. The human body could be approximated by an equivalent electrical circuit comprising a resistor connected in series to a capacitor. Touching a capacitor fiber with a finger modified the local current flow and voltage distribution, thus sensing the measured voltage to touch. Moreover, a 1 cm spatial resolution was achieved with a single fiber, thus allowing the fabrication of 2D touch-sensitive textiles with a 1D array of capacitor fibers. The fiber capacitors might also interface with other fiber electronics such as conductive fibers or battery fibers to constitute a functional on-garment electric circuit. Potential application of such on-garments electronics include fashion, safety clothes, as well as programmable and computing textiles.

Pressure-sensitive fabrics were also developed.¹⁷² To fabricate the sensors, fibers were coated with organic conductive polymer poly(3,4-ethylenedioxythiophene) and poly(styrenesulfonate) and a dielectric film of perfluoropolymer using a dye-coating system (Figure 6c). The coated fibers were woven as wefts and warps, and the rest of the matrix was filled with pristine nylon fibers. Capacitors were formed at the nodes, where the fibers intersected. When a pressure of 4.9 N cm^{-2} was applied on the fabric, capacitance increased from 0.22 to 0.63 pF with a sensitivity ranging from 0.98 to 9.80 N cm^{-2} .¹⁷²

Temperature, humidity, and pressure sensors have been incorporated in textiles.¹⁷⁴ These studies have utilized photolithography and inkjet printing to create the sensors woven into textiles (Figure 6d). Capacitive humidity and resistive temperature sensors were developed on flexible polymer foils and integrated into textiles.¹⁷³ To fabricate the sensors, metal films were deposited on polyimide sheets. In photolithography, a double metal layer of Cr/Au was electron-beam-evaporated under vacuum on polyimide sheets and patterned using a lift-off process. The sensing elements included an interdigitated thin-film capacitive transducer and a temperature-sensitive thin-film meander resistor. The inkjet printing of the sensors involved depositing Ag NP ink on the polyimide. Bus lines and interdigitated finger electrodes were printed in two separate printing steps (500–4000 dpi). The resulting line width and electrode gaps for resistors and capacitors were $80 \mu\text{m}$, and the thickness of the printed layer was 400 nm. Sensing materials were encapsulated by laminating a photoresist film on the substrate. For the detection of humidity, cellulose acetate butyrate as the sensing medium was spray-coated on the capacitor through a stencil mask. In inkjet printing, the cellulose acetate butyrate in hexyl acetate was printed over the substrate to achieve a $5 \mu\text{m}$ film. The device was capped with a hydrophobic, gas-permeable membrane. Subsequently, a commercial machine was used to weave the sensors into a textile band in the weft direction with a twill (1/8) pattern. Humidity and temperature sensors were inserted into the textile along the weft direction as a replacement for weft yarn. Warp threads were replaced by conductive yarns to contact the sensors inside the textile. The temperature sensors operated from 10 to 80°C with a sensitivity of 5°C . Humidity sensors had a detection range from 25 to 85% with 10% sensitivity.¹⁷³ These textiles were combined with LEDs to give visual sensing information (Figure 6e).¹⁷⁶ The development of electrical sensors in textiles that detect changes in resistance, capacitance, or inductance will require miniaturized chips incorporating multimeters, amplifiers, and analog-to-digital converters.

Metal–organic frameworks (MOFs) built with rare earth elements and/or quantum nanorods have been immobilized on cotton fabrics at high concentrations.¹⁷⁷ These materials have shown the potential to be used as colorimetric sensors to detect the presence of toxic gases *via* the luminescence of the MOFs or the electrical conductivity of the nanorods.¹⁷⁸ These chemical sensors can be incorporated into uniforms, apparel, or any textile substrate. A dress designed by Matilda Ceesay used cotton mesh coated with a Cu benzene tricarboxylic acid MOF-199 customized for capturing and controlled release of permethrin (an insecticide) (Figure 6f). The designer aimed at functionalizing mosquito bed-nets commonly used as preventive measures in areas with a high prevalence of malaria.¹⁷⁵

TOXICITY OF NANOMATERIALS IN TEXTILES

The forms of NPs released in washing liquid depend on the nanomaterial characteristics originally incorporated into the textile, the composition of the washing liquid, and the washing procedure (*e.g.*, rotation speed). Ag-containing textiles release significant amounts of dissolved and particulate Ag into washing liquid. The potential exposure to Ag NPs from a blanket has been evaluated. For a blanket containing $109.8 \pm 4.1 \text{ mg Ag kg}^{-1}$, $4.8 \pm 0.3 \text{ mg Ag kg}^{-1}$ was released into sweat in 1 h.¹⁷⁹ Commercial NP-impregnated socks ($1360 \mu\text{g Ag g}^{-1}$) leached up to $650 \mu\text{g}$ of Ag in distilled water (500 mL) in 24 h.⁷¹ However, other commercial socks containing large amounts of Ag (2105 and $31\,242 \mu\text{g}$) released small percentages (1 wt %) of total Ag into the ultrapure wash water while some brands released $\sim 100 \text{ wt } \%$ of the Ag after four consecutive steps. These studies indicate that the manufacturing processes of these socks differ fundamentally. The socks released 155 and $15 \mu\text{g}$ of Ag into ultrapure water and tap water, respectively. Hence, tap water was less aggressive in stripping Ag from the textile than ultrapure water, which was attributed to differences in water corrosivity.¹⁵ Artificial sweat was also used to test the concentration of the Ag released from fabrics.¹⁸⁰ The concentration of Ag released from Ag-impregnated fabrics was measured up to 322 mg kg^{-1} of fabric weight. The release rate depended on the concentration of the Ag in the fabric and pH of sweat. In another study, shirts and pants were impregnated with TiO_2 NPs ranging from 2.9 to 8.5 g Ti kg^{-1} textile.¹⁸¹ The release of TiO_2 into sweat per gram of textile after 30 min incubation in 120 mL of sweat was evaluated. Substances released into acidic sweat were $63 \pm 13 \mu\text{g g}^{-1} \text{ L}^{-1}$ (particulate size $<450 \text{ nm}$) and $725 \pm 30 \mu\text{g g}^{-1} \text{ L}^{-1}$ (particulate size $>450 \text{ nm}$), whereas in alkaline sweat, the release amounts were $38 \pm 13 \mu\text{g g}^{-1} \text{ L}^{-1}$ (particulate size $<450 \text{ nm}$) and $188 \pm 213 \mu\text{g g}^{-1} \text{ L}^{-1}$ (particulate size $>450 \text{ nm}$).¹⁹ External dermal exposure for TiO_2 was a maximal $11.6 \mu\text{g kg}^{-1}$ body weight for total (mainly particulate) TiO_2 . When Ag was released from textiles, Ag–chloro complexes were the major dissolved species due to the presence of high chloride concentration in sweat. Figure 7 shows potential scenarios for Ag release from nanomaterial-treated textiles.

The release of NPs to the environment is a concern. Ag NPs are toxic to aquatic animals, including fish, crayfish, and plankton.^{183–186} Furthermore, the antibacterial properties of Ag NPs might disrupt the bacterial habitat in sewage treatment plants.¹⁸⁷ Nanowashing machines were shown to release Ag in effluent at a concentration of $\sim 11 \mu\text{g L}^{-1}$.¹⁸⁸ Recent life cycle assessments involved comparing environmental benefits and negative effects of nanoAg T-shirts with conventional textiles treated with triclosan (a biocide).¹⁸⁹ Figure 8 shows life cycle

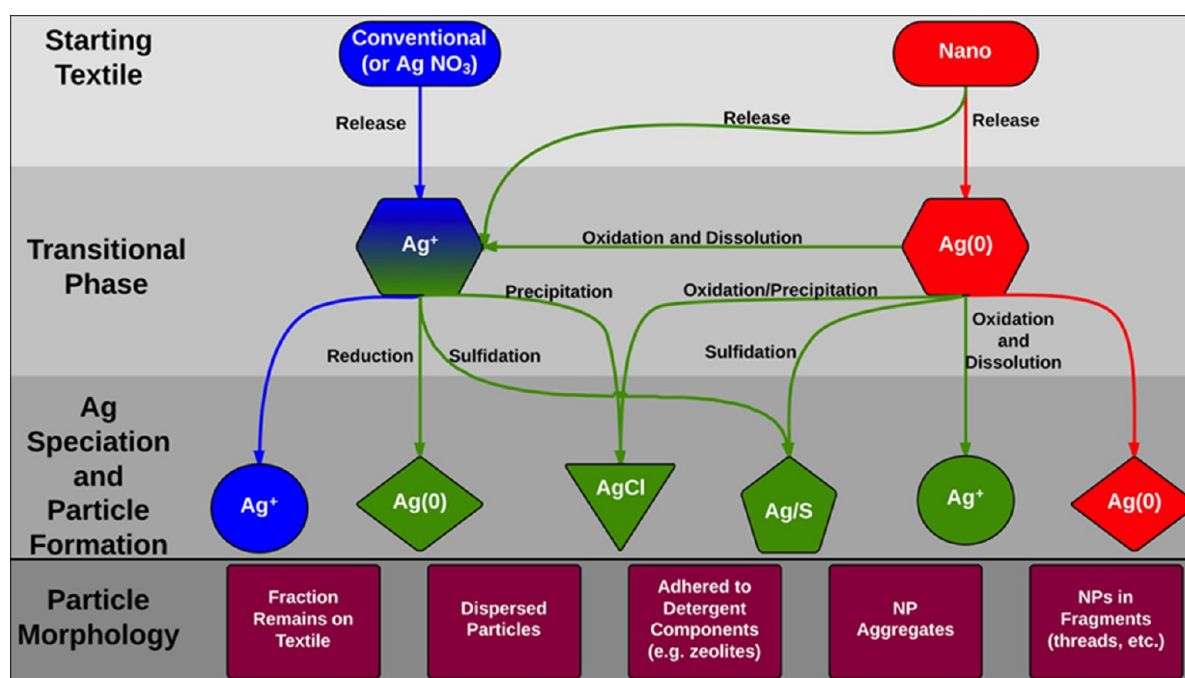


Figure 7. Scenarios for Ag release and subsequent transformation from nanomaterial-treated textiles. Blue shading indicates conventional materials or silver nitrate (AgNO_3) that persists through the transformation process, and red shading indicates pristine nanomaterials. Green shading shows a transformation product. Reprinted from ref 182. Copyright 2014 American Chemical Society.

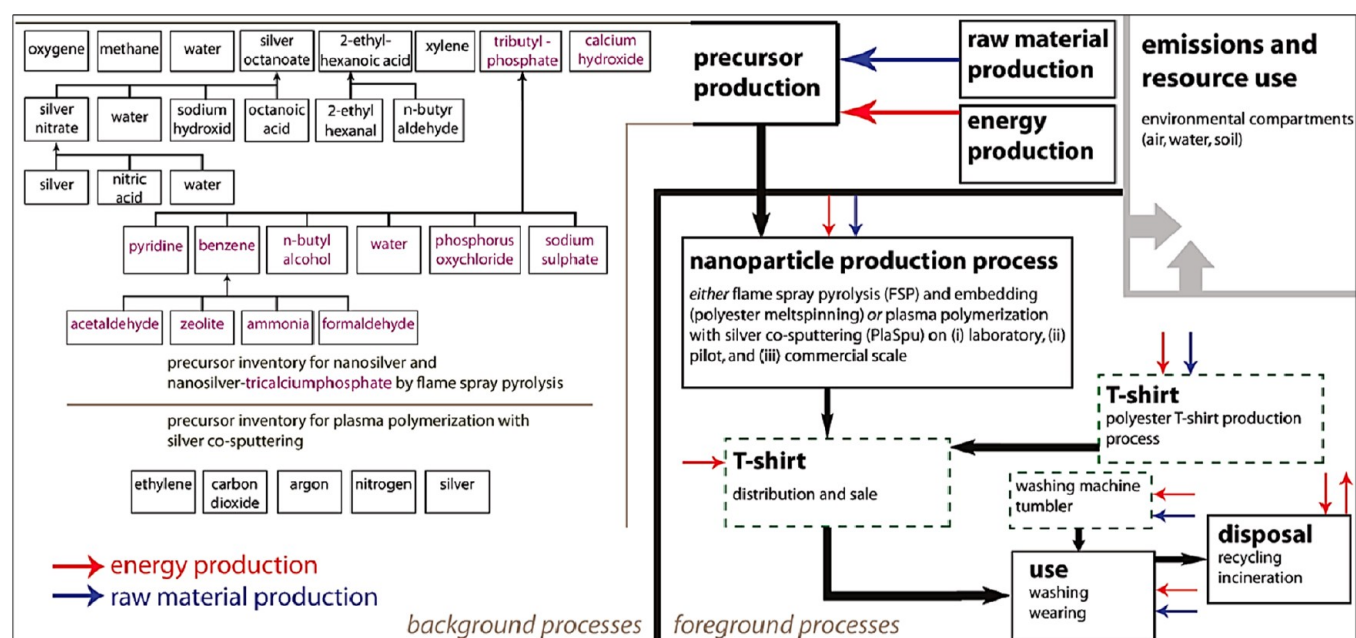


Figure 8. Life cycle stages of one nanoAg T-shirt showing system boundaries (dashed boxes). Reprinted from ref 189. Copyright 2011 American Chemical Society.

stages of one T-shirt (1.56 m^2 textile, 130 g). The “cradle-to-gate” climate footprints of the manufacturing of nanoAg T-shirt were 2.70 kg of CO_2 -equiv for flame spray pyrolysis and 7.67–166 kg of CO_2 -equiv for plasma polymerization with Ag co-sputtering. However, conventional T-shirts produced by triclosan had emissions of 2.55 kg of CO_2 -equiv. Additionally, the toxic releases from washing and disposal stages had minor relevance. However, the production phase holds importance due to toxic Ag emissions at mining sites. Overall, the use phase was the most important in terms of climate footprint in both

nanoAg and triclosan cases. A limitation of these studies was that variation in Ag release rates was not taken into consideration. Also, current life cycle impact assessment methods do not distinguish colloiddally bound phases of metals.^{190,191} Until now, the life cycle assessments took into account only NP form. Considering other forms of nanomaterials, such as ionic forms, agglomerated forms, and oxidized forms, will provide improved life cycle assessments. While these assessments provide an estimated effect of nanomaterials on the environment, public awareness holds importance in washing

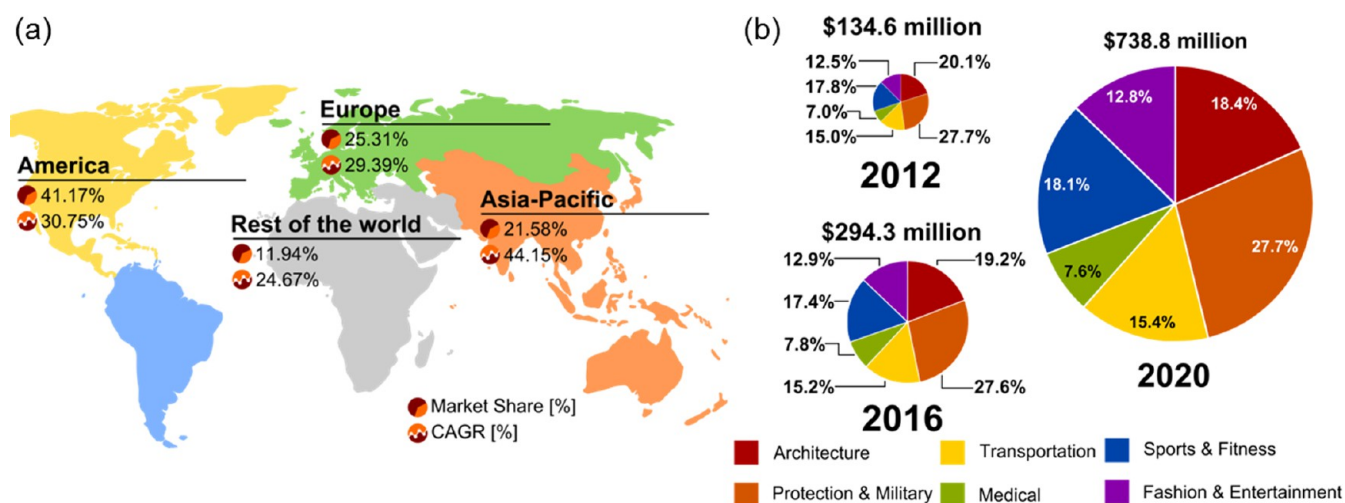


Figure 9. Smart textiles market. (a) Market shares and CAGRs by region in 2014. (b) North America smart textiles market revenue by end use, 2012–2020.

practices. For example, efficient washing procedures such as using tumblers less and operating the washing machine at lower temperatures with appropriate detergents may reduce the environmental impact. The increase in the awareness for recycling rate of NP-embedded textiles may decrease the carbon footprint. Furthermore, exposure to NPs is a significant concern in the workplace.¹⁹² For example, spraying methods may result in exposure to inhalation of NPs.¹⁹³ The development of improved life cycle assessments will allow comparing nanoengineered textiles with conventional products in the market to prevent negative environmental consequences.

CONSOLIDATION OF NANOTECHNOLOGY IN THE TEXTILES MARKET

Fashion and apparel industries were valued at \$1.2 trillion globally in 2014, and the market size is expected to have a compound annual growth rate (CAGR) of 4.8% until 2025, mainly driven by emerging markets.^{194,195} In the United States, 1.9 million people are employed and \$250 million are spent in the fashion industry annually.²⁴ In 2014, the global smart textiles market was assessed at \$795 million, which is anticipated to reach \$4.72 billion by 2020 with a CAGR of 33%.¹⁹⁶ Major drivers for the smart textiles market are wearable electronics, increasing demand for devices with advanced functions, miniaturization of electronics, and rapid growth of low-cost wireless sensor networks. Military and security sectors have the largest shares of the smart textiles, accounting for about 27% of the total market. The market shares for the sports and fitness segments are expected to increase at a CAGR of 40% until 2020.¹⁹⁶ The Americas was accounted for 41% of the global smart textiles market in 2014, followed by Europe (25%) and Asia-Pacific (21%) in 2014 (Figure 9).¹⁹⁶ However, the Asia-Pacific market is expected to have the highest CAGR (44%) in the next 5 years. The United States' market is projected to grow at a CAGR of 31% until 2020.¹⁹⁶ High growth rates may be attributed to trends outside conventional apparel. This is because, in traditional apparel, there is more demand for cost reduction, as opposed to performance enhancement. In the case of innovative and functional applications of wearables, the customer motivation is opposite.¹⁹⁷ Furthermore, the market for nanofiber-based products is expected to reach over \$1 billion by 2020.¹⁹⁸

However, this market is not limited to the textile and apparel industry.^{196,199} With a demanding market for wearables and a growing trend for nanofiber-based products, the applications are diverse for nanotextile products ranging from consumer apparel to medical wearables.²⁰⁰

A driving force for the smart textiles industry is sensing technologies with Internet connection. This capability can be used to communicate data such as location as well as physiological parameters (e.g., heart rate), which are important in healthcare, sports, and fitness. Therefore, this trend is expected to affect the market globally. For example, the use of functional materials in textiles has led to electrophysical characteristics such as piezoresistivity and conductivity. These technologies aim to evaluate the patient's synoptic data. The process involves the development of smart textiles, communicating the data over the network, and using it to make informed decisions. One of the challenges facing the apparel industry in the use of such communication devices is ensuring simultaneous wearability and functionality of efficient and portable power supplies.

In general, fashionable functional products transcending the traditional functions of fabric are highly desirable. Growth in the fashion and entertainment industry is expected to contribute to overall market growth. Additionally, the demand from the sports and fitness sector has increased due to growing awareness about healthy lifestyles. End users participating in extreme sports, running, and skiing have also contributed to the demand for smart textiles. To increase the competitiveness with respect to Asia, the European Union has created initiatives for promoting incentives.²⁰¹ The European Commission has co-financed a number of projects such as Wealthy, MyHeart, and Biotex. For example, Wealthy aims to create a wearable device for monitoring patient's vital signs.

To meet a wide range of end user needs, it is vital to market wearables that offer various levels of performance and comfort to a wide customer base. The necessity for various levels of performance stems from global customers who are willing to pay a premium price for functional garments. However, in another market segment, the target customer may demand affordable functional textiles. One possible reason for the interest in innovation in textiles is that porous materials, synthetic microfibers, and membranes used commercially over

the past 30 years have been commodified. This may be attributed to the accessibility of blockbuster technologies due to patent expirations. The commodification subsequently reduced the profit margin and market share.¹⁹⁸ As a result, companies in the textile industry need to offer competitive advantage through innovation by either enhancing performance or reducing the production cost.

CASE STUDIES

Gore-Tex is a lightweight, waterproof, breathable fabric membrane comprising expanded polytetrafluoroethylene (ePTFE) for application in medical devices, fabrics, and electronics.^{43,202} W. L. Gore & Associates (Newark, DE) invented ePTFE in the 1970s. Gore-Tex was originally a microporous structure that could be stretched up to 800% of its original length.²⁰³ Gore-Tex is used in products manufactured by various enterprises including Patagonia, L.L. Bean, Oakley, Inc., Galvin Green, Marmot, Vasque, Arc'teryx, Haglöfs, and The North Face.^{204,205} W. L. Gore & Associates holds more than 71 issued patents related to Gore-Tex or the use of PTFE, in which 18 patents are for use in garments. Although the basis for the Gore-Tex technology originated from microporous structures, the company has recently incorporated nanostructures into their products for the apparel market. For example, Nano and NanoPro jackets have been manufactured in conjunction with Marmot LLC.²⁰⁶ Other nanotechnology-based examples could be seen in the company's patent portfolio. Examples include Nygraph 351 (Nyacol Nano Technologies, Inc.) for burn protective materials,²⁰⁷ nano-emulsions of functionalized PTFE,²⁰⁸ prefiltration layers comprising nanofibers,²⁰⁹ and NPs for improved insulated electrical conductors.²¹⁰ These cases serve to illustrate the importance of nanotechnology to a well-established innovative company in the apparel industry.

NanoSphere marketed by Schoeller Textiles AG (Sevelen, Switzerland) is a finishing technology with hydrophobic surface properties that mimic the self-cleaning effect of lotus leaves.³⁸ Schoeller claims that NanoSphere has improved water/oil- and dirt-repelling properties and washing performance compared to traditional textile impregnation-based manufacturing. Furthermore, the protective function of NanoSphere may be retained after frequent use and numerous washing cycles without affecting comfort, texture, and breathability. The textiles finished with NanoSphere require less frequent washing at lower temperatures as compared to conventional textiles. Additionally, it has high abrasion resistance. The company's other products address a variety of applications ranging from stretch fabrics, sun reflectors, temperature resistance, and bionic climate conditioning.²¹¹ Their patent portfolio in nanotechnology includes PEIN NPs for antibacterial finishing of electrospinnable polymers,²¹² NPs and CNTs for finishing of substrates,²¹³ and nanofibers having microbicidal properties.²¹⁴

Aquapel, marketed by Nanotex LLC (Bloomfield Hills, MI), reproduces natural water repellency of plant surfaces and animal coats.¹⁷⁷ Aquapel technology involves permanent attachment of hydrophobic "whiskers" to individual fibers at the molecular level. Aquapel features a hydrocarbon polymer that is ecologically friendly and low cost. Nanotex's portfolio consists of 28 WO patent applications and addresses textile sectors including repellency/stain resistance, moisture management, odor control, static elimination, and wrinkle resistance. In 2013, Nanotex products were at \$280 million in branded

products at retail.⁹ In the same year, Nanotex was acquired by soft-surface technology company Crypton Inc.²¹⁵

SmartSilver is an antimicrobial yarn marketed by Nano-Horizons (Bellefonte, PA). It develops and manufactures Ag NP additives that provide antimicrobial characteristics to their products. The company markets Oeko-Tex antimicrobial solution under the SmartSilver brand.^{216,217}

Nanosan, marketed by SNS-Nano Fiber Technology (Hudson, OH) and Schill & Seilacher (Germany), consists of spun polymers for application in filters and adsorbent fabrics.²¹⁸ SNS-Nano Fiber Technology integrates microscale particles into the nanofiber structure at high-volume production. Nanosan fibers can be engineered to function as high-strength, absorbent, or flexible material. Its product line consists of nanofiber matrixes with different absorption properties. The applications of Nanosan include filters, medical and military products, and personal care products such as cosmetics. Its patent portfolio includes debris and particle-absorbent materials.^{219–222} The company is currently exploring the use of nanofibers for skin decontamination.

Wearable Motherboard (electronic shirt), marketed by Sarvint Technologies, Inc. (Atlanta, GA), uses engineered fibers to sense body signs, such as heart rate, temperature, skin conductivity, muscle exertion, blood pressure, and respiration rate.¹⁵⁵ Its patent portfolio includes the use of engineered fabric-based sensors (e.g., conductive fibers) for monitoring vital signs. Its technology comprises microporous elastic Spandex fiber, a polyester–polyurethane copolymer invented in 1958.^{223–225} Table 1 shows the companies involved in smart textiles and wearables market.²²⁶ Some of these companies use microtechnology as opposed to nanotechnology in apparel.

FUTURE DIRECTIONS

The integration of high-computing microprocessors and miniaturized computers can enable the capability to collect information throughout a garment. For example, the physiology of the body and posture data collection in garments could allow for correcting the unhealthy posture. Wearing high heels shifts the center of gravity forward, and this causes disturbances in the posture. This produces strains on the calf muscles and thigh muscles and a forward tilt in the pelvis. These changes have negative implications in the body including misalignment of hips and spine and increase in the pressure on the forefoot, leading to degenerative arthritis in the knee. New wearable technologies can be incorporated in garments and shoes to measure the pressure and posture pattern and alert the user. Such technologies can loosen or stiffen the dress or shoe based on the motion to prevent pain or sag. Weight loss is another potential area that can be explored with nanomaterials. For example, vibration motors can be integrated in textiles to promote blood circulation and weight loss. These devices may also achieve wireless powering of the internal or external electrical components. For example, self-winding mechanisms developed in automatic watches can be utilized to generate energy from the movement of the body. A significant area that nanotechnology-based energy sources can provide a solution for is cooling. Highly dense fabric batteries or solar cells need to be developed for power cooling without compromising comfort. Such powering mechanisms can be coupled with phase-change materials to cool the body in hot environments or cool the electronic components in the textile.

Interactive garments in fashion will also evolve. Programmable visual components, LEDs, and fiber optics in garments

Table 1. Companies That Have Commercialized Micro- and Nanotechnology-Based Apparel, Their Major Products, and Applications

company	year founded	number of pending patents/granted	area (micro/nano)	technology and products	applications	ref
Auxetic Technologies Ltd. (UK)	2004	3	micro/nano	auxetic materials (becomes thinner when stretched and thicker when compressed)	composite material, auxetic foams	227–229
Brandix Lanka Limited (Sri Lanka)	2002	N/A	nano	functional clothing	fabric and garment accessories	N/A
Clothing Plus Ltd. (Finland)	2001	2	micro	heart rate sensing shirt (combined textiles and electronics)	comfortable biometric sensor electronics for sports and medical applications	230,231
DuPont (USA)	1802 (sold its textiles business to Koch Industries in 2004)	>100, out of which 32 are related to garment	micro/nano	Lyera (Spandex), a stretch fiber	stretchable, compression and shaped garments, home furnishings	232–241
Exo2 (USA)	2007	N/A	nano	FabRoc and ThermoKnitt heating technology	wireless heated outdoor clothing	N/A
FibeRio Technology Corporation (USA)	2009	2	micro/nano	micro- and nanofibers	apparel, filtration, healthcare, and electronics	242,243
Fibretronic limited (Hong Kong)	2004	N/A	micro	textile electronics	wearable electronics and smart fabrics (sensors, heating, and cooling elements)	N/A
Freudenberg Group (Germany)	1849	N/A	micro/nano	housewares and cleaning products, automobile parts, and textile	nonwoven fabrics and textile materials	N/A
Gentherm Incorporated (USA)	1960	18	micro	heating and cooling comfort	thermoelectrically heated and cooled seat system (automotive, medical, bedding)	244–253
Google Inc. (USA)	1998, partnered with Levi Strauss & Co.	N/A	micro	jacquard: a microfiber-woven textile	textile with digital sensing microfibers	N/A
Hollingsworth and Vose (USA)	1843	3	micro/nano	filtration and nonwoven materials	composite materials, home furnishings, apparel	254–256
HeiQ (Switzerland)	2005	6	micro/nano	dynamic cooling, water and oil repellency on textiles	outdoor products, medical implants	257–263
Interactive Wear AG (Germany)	2005	2	micro	functional textile products: textile cable, heating pads, interactive wearable solar energy source	integrated textile systems	264,265
International Fashion Machines, Inc. (USA)	2002	2	micro	electronically controllable flexible substrate	electronic textiles, which behave as an electronic circuit or device	266,267
Midé Technology Corporation (USA)	1989	11	micro	piezo cooling, haptic actuators, energy harvesting, data logging	general wearables	268–278
Nanohorizons (USA)	2002	2	nano	Ag NPs	NanoAg textiles	216,217
Nanotex (USA)	1998	22	nano	nanoengineered polymers	moisture resistance, odor management	279–300
Ohmatex Aps (Denmark)	2004	N/A	micro	elastic textile cables, conductive textiles, textile-based sensors	textiles combined with IT technology	N/A
Peratech Ltd. (UK)	1996	12	nano	electroactive polymeric material QTC (Quantum Tunneling Composites)	force and touch sensing within electronic circuits	301–312
Sarvant Technologies, Inc. (USA)	2014	6	micro/nano	functional wearables	garment with intelligence capability	224,225,313–316
Schoeller Textiles AG (Germany)	1967	9	micro/nano	stretchable fabrics, protection fabrics, soft shells, protective fabrics	NP-containing fibers	212–214,317–322
Sensium Healthcare (UK)	2000	N/A	micro	SensiumVitals, a lightweight patch reading of patients' heart rate, respiration, and temperature	wireless monitoring of vital signs	N/A
Sensoria Inc. (USA)	2010	3	micro	body-sensing wearable devices	anklet and sensor infused socks and fitness bras and T-shirts with heart rate monitor	323–325
SNS Nano (USA)	2007	4	nano	debris and particle absorbent materials	textile composite material	219–222

Table 1. continued

company	year founded	number of pending patents/granted	area (micro/nano)	technology and products	applications	ref
Texas Instruments (USA)	1951	>100	micro	semiconductors, microcontrollers DLP products and MEMS	wearable displays, Bluetooth wearable watch	N/A
Textronics, Inc. (USA)	2005	13	micro/nano	NuMetrex, soft textile sensors	health and fitness monitoring	326–331
Thermosoft International (USA)	1996	6	micro	flexible electric heaters	heated fabric, conductive textile, heated bedding and clothing	332–343
VivoMetrics Inc. (USA)	2009	8	micro	body worn sensors: Hexoskin (sports shirt), Nonin (wrist-worn Bluetooth pulse oximeter), Onyx (finger clip wireless pulse oximeter), LifeShirt (garment with embedded sensors)	continuous ambulatory physiological monitoring sensor systems	344–351
Wearable Information Technologies (Wear-tech) (Spain)	2007	1	micro	smart fabrics and interactive textiles	sports, fitness, health prevention, healthcare, and industrial safety	352
W. L. Gore & Associates	1958	48 (Gore-Tex or PTFE): 13 in garments	micro/nano	Gore-Tex is a waterproof, breathable fabric membrane	widespread products, including fashion and apparel	203,353–371

will find increasing use in fashion and entertainment industries. Incorporation of new approaches including structural colors, luminescence, plasmonics, metamaterials, holography, photonic crystals (PCs), and LED displays in textiles can create mesmerizing effects on garments. These dresses can be combined with pressure or motion sensors that can change the color of the dress based on touch, movement, temperature, light, electric field, or other external stimuli. The material may also include bioinspired patterns and chemical reactions with the environment.

In addition to serving as light-emitting elements to enable the shining and colorful appearance for fashion apparel, optical fibers offer more capabilities. For example, an array of fibers can be weaved into a garment to constitute a programmable fiber-optic display that is able to show dynamic graphics. Optical fibers can also be used as sensing components in multifunctional garments for sports and fashion. Recently, Cambridge Consultants has developed Xelflex fabric that was equipped with optical fiber sensors for tracking movements of the human body.³⁷² Xelflex could be used in fitness and sports coaching as well as part of physiotherapy. Additionally, fiber-sensor-based gloves and garments that can recognize postures of the human hand and body have been demonstrated.³⁷³ Physical or chemical stimuli such as strain, pressure, temperature, humidity, and metabolites may be detected by on-garment fiber sensors.³⁷⁴ Thus, in the near future, a fully functionalized sportswear based on fiber-optics sensors will be produced for monitoring physiological conditions of the human body including heart rate, blood pressure, sweating, body motions, temperature, and even potential disease risks. Such garments can also be used for increasing the interaction and connectivity of the user with gaming consoles and virtual reality platforms.

Integration of optical displays into textiles or garments is desirable for many applications. Current textile displays are mostly based on LEDs. Although LEDs are low cost, small, and available in an array of different colors, they are not truly compatible with textiles due to their rigidity. Additionally, the resolution of the LED textile displays is typically low (LED pitch = 1–100 mm).³⁷⁵ The LCDs that are commonly used in current smartphones, tablets, and computers are usually inflexible.³⁷⁶ Considering the flexibility and light weight required for textile displays, OLEDs composed of thin films of organic molecules constitute a potential candidate.³⁷⁷ Another promising technology for the fabrication of textile displays is quantum-dot light-emitting diodes (QLEDs), which are similar to OLEDs in structure but have an additional active layer consisting of quantum dots.^{378,379} In textile displays, QLEDs could offer higher luminance efficiency and consume less energy than OLEDs. These technologies may be combined with optical components such as diffraction gratings, diffusers, lenses, or microcavities.^{380–383}

Photonic crystals are nanostructures in which the dielectric constant has a periodic variation in one, two, or all three orthogonal directions.^{384–386} In such structures, one observes formation of the spectral photonic band gaps, which are the spectral regions where photons are unable to propagate in the bulk of the periodic structure. Therefore, narrow-band colors could be seen in the light diffracted or transmitted by PCs. They can be incorporated into flexible thin films that may be conveniently attached to a fabric or garment.^{387,388} These PC films can change their color when stimulated by external stimuli such as current, compression, stretch, or temperature and humidity. The structural parameters of PCs or the effective

refractive index of PCs are modified by these stimuli, thus shifting the PC spectral band gaps.^{389,390} This color-tuning property may be utilized for garments to not only promote the aesthetic performance but also enable sensing applications.³⁹¹

Combining holograms with garments and wearable devices is another potential research direction.^{392,393} A hologram is first produced by encoding interference information on an object on a recording medium. A 3D image of the recorded object can be reconstructed by illuminating the holographic film with a broadband light.^{394,395} To date, a variety of holographic films have been used as decorative coatings that were able to provide garments with iridescent appearances and 3D graphics.¹⁴⁴ Holograms may also be used in other wearable gadgets such as helmets and glasses for virtual reality applications. In Hololens (Microsoft), holographic gears are equipped on a headset.³⁹⁶ Thus, wearers of Hololens may appreciate a virtual life experience by visualizing and interacting with the environment on demand. Moreover, holographic sensors that are fabricated into thin films could also be integrated into garments for detecting metabolic function.^{397–402}

Metamaterials are artificial structured substances made by assembling composite materials such as metals and plastics in periodic patterns at scales that are smaller than the wavelength of interest.⁴⁰³ Metamaterials due to their extraordinary structures exhibit complex behavior to electromagnetic waves (e.g., negative refractive index). Many intriguing features could be offered by metamaterials when used in textiles and garments. For example, metamaterials have potential for the development of cloaking devices that are used to make a defined region invisibly isolated from the passing electromagnetic waves. While some progress on metamaterial-based cloaking devices was made at microwave⁴⁰⁴ and THz frequencies,^{405,406} truly invisible garments may be realized in the visible spectral region. Moreover, many thin-film metamaterial sensors have been demonstrated.⁴⁰⁷ These sensors could be potentially integrated into textiles and garments for monitoring physiological biomarkers.

Nanotextiles can be functionalized with molecular dyes and analyte-sensitive compounds. For example, microfluidics can be incorporated in thread-based channels for application in point-of-care diagnostics.^{408–416} In the future, many functional components may be seamlessly integrated into textile architecture. Accordingly, production processes will also evolve to combine electronics, biomaterials, and optics into textile weaving. Applications in fashion and arts will also be realized.^{417,418} These sensing and display technologies may be controlled by smartphones.^{419–421}

Another potential research area is to create green chemistries and fabrication approaches to synthesize nanomaterials that stay intact after laundering. For example, development of new covalent binding mechanics to attach nanomaterials to cotton or synthetic fibers is desirable. These nanomaterials may also require new surface-finishing processes to ensure their immobilization in textiles and maintenance in any environmental condition. Additionally, agglomeration of deposited nanomaterials is a major challenge, and this requires the development of new nanoadditives and stabilizers in formulations and finishing treatments. These approaches may require functional surface-activated polymer or cotton composites to immobilize nanomaterials on the textile without compromising their chemical, optical, and electrical properties. Furthermore, recycling of clothing is generally carried out by creating landfills. A significant concern about the nanomaterials

is potential contamination of water or soil.¹⁸² Hence, life cycle assessments should also focus on identifying risk factors for laundering, recycling, and particle release after degradation while accounting for different forms of NPs and release rates. The effects of uncontrolled release of nanomaterials to the environment and toxicity to humans and marine life need to be evaluated before the introduction of nanoproducts to the market. Since these nanomaterial-based textiles are likely to be produced in the emerging economies, the safety of the workers and exposure to nanomaterials warrant nanotoxicity analyses. The commercialization of nanotechnology-based textiles may be limited due to government regulations. For example, biocidal textiles containing nanoAg are registered by the Environment Protection Agency (EPA) in the United States.¹⁹¹ ISO catalogue enlists a number of standards for formulating and testing nanoproducts.⁴²²

CONCLUSIONS

The customer demand in improved appearance, functionality, and connectivity in fashion has motivated the development of nanotechnology-based textiles. Over the last two decades, numerous nanostructures and nanomaterials including NPs, CNTs, Bragg diffraction gratings, and nanoelectronic components have been deposited or woven into textiles. The development of these nanomaterials also create new fabrication methods involving particle impregnation, spray coating, multi-functional composite fiber drawing, and direct weaving at an industrial scale. The application of nanomaterials in the form of surface modifications, electronics, and optics offers functionality as well as the potential of improved appearance. Realized nanotechnology applications in textiles include antibacterial properties, odor control, UV protection, water repellence, wrinkle resistance, antistatic properties, and strength enhancements. Advanced technologies included incorporation of moisture, temperature, pressure sensors, drug release, and fiber optics powered by textile-based batteries. With the emergence of nanomaterials, these technologies are transitioning from rigid to seamlessly integrated flexible substrates while offering light weight.

In parallel to the development of nanotextiles, life cycle assessments and toxicity of released nanomaterials from textiles are being critically evaluated. Nanotechnology-based products will continue to emerge with new applications; however, manufacturers and regulatory agencies must ensure that these technologies will not have a negative effect on human health and the planet during their manufacture and life cycle. The textile industry is under scrutiny due its impact on climate change.⁴²³ Today, textiles and apparel account for ~10% of the total carbon emissions.⁴²⁴ 17–20% of industrial water pollution originates from dyeing and finishing agents in the textile industry, negatively affecting people inhabiting regions around textile production plants, particularly in the developing world.⁴²⁵ Dyes and fixing agents (e.g., chromium) in textile manufacturers and tanneries are major pollutants, particularly in Southeast Asia.⁴²⁶ Hence, the effect of nanoproducts on the production dynamics and pollution remains questionable. Growing concerns among customers has begun forcing the manufacturers to reduce the environmental impact of their production methods, which will also involve the use of nanomaterials.^{427,428} Social awareness among customers has probed companies to invest in corporate social responsibility to offer environmentally sustainable products with reduced carbon footprints.^{429–431} These trends in customer behavior and

climate change will include the use of nanotextiles, which need to be climate neutral and recyclable aimed at reducing greenhouse emissions. Nanotechnology will undoubtedly evolve textiles, transcending style changes to shape the next big concept: the connected couture.

AUTHOR INFORMATION

Corresponding Authors

*E-mail: ayetisen@mgh.harvard.edu.

*E-mail: syun@mgh.harvard.edu.

Author Contributions

A.K.Y. designed the project and wrote the article. H.Q. contributed to Photonic Technologies for Textiles. A.M. contributed to Market and Case Studies sections. S.H.Y., A.K., M.R.D., H.B., J.H., and M.S. made intellectual contributions and edited the manuscript.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

We thank Philipp Walch and Huseyin Avci for discussions.

VOCABULARY

Wearables, electronics, fiber optics, or nanomaterials embedded in clothing and accessories that offer improved mechanical, chemical, and optical performance *via* sensing external stimuli and/or responding to the environment; **Warp**, to arrange threads in long lengths parallel to one another in preparation of further processing; **Weft**, threads widthways in a fabric as woven; **Finishing**, a process performed on yarn or fabric after weaving to improve the look, performance, or texture of the finished textile; **Lotus effect**, self-cleaning due to hydrophobicity induced by nano or microscale hierarchical structured surfaces; **Supercapacitor**, an electrochemical cell that allows storing electrical energy temporarily; **Photonic band gap material**, a nano- or microscale structure that controls the optical properties of incident light; **Electromagnetic shielding**, blocking the electromagnetic field by conductive or magnetic materials; **Bragg fiber**, fiber optics incorporating Bragg gratings to filter narrow-band light

REFERENCES

- (1) Cherenack, K.; van Pieterse, L. Smart textiles: challenges and opportunities. *J. Appl. Phys.* **2012**, *112*, 091301.
- (2) Sawhney, A.; Condon, B.; Singh, K.; Pang, S.; Li, G.; Hui, D. Modern applications of nanotechnology in textiles. *Text. Res. J.* **2008**, *78*, 731–739.
- (3) Gould, P. Textiles gain intelligence. *Mater. Today* **2003**, *6*, 38–43.
- (4) Paradiso, R.; Loriga, G.; Taccini, N.; Gemignani, A.; Ghelarducci, B. Wealthy-a wearable healthcare system: new frontier on e-textile. *J. Telecomm. Inf. Technol.* **2005**, 105–113.
- (5) Cheng, M.-H.; Chen, L.-C.; Hung, Y.-C.; Yang, C. M. In A real-time maximum-likelihood heart-rate estimator for wearable textile sensors, Engineering in Medicine and Biology Society, 2008. EMBS 2008. 30th Annual International Conference of the IEEE, IEEE **2008**, 254–257.
- (6) Mattmann, C.; Amft, O.; Harms, H.; Tröster, G.; Clemens, F. Recognizing Upper Body Postures Using Textile Strain Sensors. In *11th IEEE International Symposium on Wearable Computers*; Boston, MA, 2007; pp 29–36.
- (7) Jung, S.; Lauterbach, C.; Strasser, M.; Weber, W. Enabling technologies for disappearing electronics in smart textiles. *Proceedings of IEEE ISSCC03* **2003**, *1*, 386–387.

- (8) Catrysse, M.; Puers, R.; Hertleer, C.; Van Langenhove, L.; Van Egmond, H.; Matthys, D. Towards the integration of textile sensors in a wireless monitoring suit. *Sens. Actuators, A* **2004**, *114*, 302–311.
- (9) Hu, L.; Cui, Y. Energy and environmental nanotechnology in conductive paper and textiles. *Energy Environ. Sci.* **2012**, *5*, 6423–6435.
- (10) Brown, P.; Stevens, K. *Nanofibers and Nanotechnology in Textiles*; Woodhead Publishing: Cambridge, UK, 2007.
- (11) Hinestroza, J. P. Can nanotechnology be fashionable? *Mater. Today* **2007**, *10*, 64.
- (12) Avila, A. G.; Hinestroza, J. P. Smart textiles: Tough cotton. *Nat. Nanotechnol.* **2008**, *3*, 458–459.
- (13) Russell, E. Nanotechnologies and the shrinking world of textiles. *Textile Horizons* **2002**, *9*, 7–9.
- (14) Marmur, A. The lotus effect: superhydrophobicity and metastability. *Langmuir* **2004**, *20*, 3517–3519.
- (15) Gao, L.; McCarthy, T. J. The “lotus effect” explained: two reasons why two length scales of topography are important. *Langmuir* **2006**, *22*, 2966–2967.
- (16) El-Khatib, E. Antimicrobial and Self-cleaning Textiles using Nanotechnology. *Res. J. Text. Apparel* **2012**, *16*, 156–174.
- (17) Zhang, J.; France, P.; Radomyselskiy, A.; Datta, S.; Zhao, J.; van Ooij, W. Hydrophobic cotton fabric coated by a thin nanoparticulate plasma film. *J. Appl. Polym. Sci.* **2003**, *88*, 1473–1481.
- (18) Bae, G. Y.; Min, B. G.; Jeong, Y. G.; Lee, S. C.; Jang, J. H.; Koo, G. H. Superhydrophobicity of cotton fabrics treated with silica nanoparticles and water-repellent agent. *J. Colloid Interface Sci.* **2009**, *337*, 170–175.
- (19) Yu, M.; Gu, G.; Meng, W.-D.; Qing, F.-L. Superhydrophobic cotton fabric coating based on a complex layer of silica nanoparticles and perfluorooctylated quaternary ammonium silane coupling agent. *Appl. Surf. Sci.* **2007**, *253*, 3669–3673.
- (20) Synytska, A.; Khanum, R.; Ionov, L.; Cherif, C.; Bellmann, C. Water-repellent textile via decorating fibers with amphiphilic janus particles. *ACS Appl. Mater. Interfaces* **2011**, *3*, 1216–1220.
- (21) Liu, Y.; Chen, X.; Xin, J. Hydrophobic duck feathers and their simulation on textile substrates for water repellent treatment. *Bioinspiration Biomimetics* **2008**, *3*, 046007.
- (22) Liu, Y.; Tang, J.; Wang, R.; Lu, H.; Li, L.; Kong, Y.; Qi, K.; Xin, J. Artificial lotus leaf structures from assembling carbon nanotubes and their applications in hydrophobic textiles. *J. Mater. Chem.* **2007**, *17*, 1071–1078.
- (23) Ramaratnam, K.; Tsyalkovsky, V.; Klep, V.; Luzinov, I. Ultrahydrophobic textile surface via decorating fibers with monolayer of reactive nanoparticles and non-fluorinated polymer. *Chem. Commun.* **2007**, 4510–4512.
- (24) Shyr, T.-W.; Lien, C.-H.; Lin, A.-J. Coexisting antistatic and water-repellent properties of polyester fabric. *Text. Res. J.* **2011**, *81*, 254–263.
- (25) Lam, Y. L.; Kan, C. W.; Yuen, C. W. M. Effect of concentration of titanium dioxide acting as catalyst or co-catalyst on the wrinkle-resistant finishing of cotton fabric. *Fibers Polym.* **2010**, *11*, 551–558.
- (26) Liu, Y.; Wang, X.; Qi, K.; Xin, J. Functionalization of cotton with carbon nanotubes. *J. Mater. Chem.* **2008**, *18*, 3454–3460.
- (27) Wang, R.; Xin, J.; Tao, X. UV-blocking property of dumbbell-shaped ZnO crystallites on cotton fabrics. *Inorg. Chem.* **2005**, *44*, 3926–3930.
- (28) Xue, C.-H.; Chen, J.; Yin, W.; Jia, S.-T.; Ma, J.-Z. Superhydrophobic conductive textiles with antibacterial property by coating fibers with silver nanoparticles. *Appl. Surf. Sci.* **2012**, *258*, 2468–2472.
- (29) Artus, G. R.; Zimmermann, J.; Reifler, F. A.; Brewer, S. A.; Seeger, S. A superoleophobic textile repellent towards impacting drops of alkanes. *Appl. Surf. Sci.* **2012**, *258*, 3835–3840.
- (30) Hoefnagels, H.; Wu, D.; De With, G.; Ming, W. Biomimetic superhydrophobic and highly oleophobic cotton textiles. *Langmuir* **2007**, *23*, 13158–13163.
- (31) Dong, W.; Huang, G. Research on properties of nano polypropylene/TiO₂ composite fiber. *J. Textile Res.* **2002**, *23*, 22–23.

- (32) Zhou, Z.; Chu, L.; Tang, W.; Gu, L. Studies on the antistatic mechanism of tetrapod-shaped zinc oxide whisker. *J. Electrostat.* **2003**, *57*, 347–354.
- (33) Wu, Y.; Chi, Y.-b.; Nie, J.-x. Preparation and application of novel fabric finishing agent containing nano ATO. *Gongneng Gaofenzi Xuebao* **2002**, *15*, 43–47.
- (34) Xu, P.; Wang, W.; Chen, S. Application of nanosol on the antistatic property of polyester. *Melliand Int.* **2005**, *11*, 56–59.
- (35) Shishoo, R. Recent developments in materials for use in protective clothing. *Int. J. Cloth. Sci. Technol.* **2002**, *14*, 201–215.
- (36) Textor, T.; Mahltig, B. A sol–gel based surface treatment for preparation of water repellent antistatic textiles. *Appl. Surf. Sci.* **2010**, *256*, 1668–1674.
- (37) Zhang, F.; Yang, J. Preparation of nano-ZnO and its application to the textile on antistatic finishing. *Int. J. Chem.* **2009**, *1*, 18–22.
- (38) Qiaozhen, Y. Influence of nano-particles treatment on the antistatic property of polyester fabric. *J. Textile Res.* **2007**, *12*, 19.
- (39) Wang, D.; Lin, Y.; Zhao, Y.; Gu, L. Polyacrylonitrile fibers modified by nano-antimony-doped tin oxide particles. *Text. Res. J.* **2004**, *74*, 1060–1065.
- (40) Chien, H.; Chen, H.; Wang, C. The study of non-formaldehyde crease-resist finishing fabrics treated with the compound catalyst of nanometer grade TiO₂ under UV light and different polycarboxylic acid. *J. Hwa Gang Textile* **2003**, *10*, 104–114.
- (41) Wang, C. C.; Chen, C. C. Physical properties of crosslinked cellulose catalyzed with nano titanium dioxide. *J. Appl. Polym. Sci.* **2005**, *97*, 2450–2456.
- (42) Yuen, C.; Ku, S.; Kan, C.; Cheng, Y.; Choi, P.; Lam, Y. Using nano-tio 2 as co-catalyst for improving wrinkle-resistance of cotton fabric. *Surf. Rev. Lett.* **2007**, *14*, 571–575.
- (43) Lam, Y.; Kan, C.; Yuen, C. Wrinkle-resistant finishing of cotton fabric with BTCA—the effect of co-catalyst. *Text. Res. J.* **2011**, *81*, 482–493.
- (44) Yuen, C.; Ku, S.; Li, Y.; Cheng, Y.; Kan, C.; Choi, P. Improvement of wrinkle-resistant treatment by nanotechnology. *J. Text. Inst.* **2009**, *100*, 173–180.
- (45) Lu, Y.; Lin, H.; Chen, Y.; Wang, C.; Hua, Y. Structure and performance of Bombyx mori silk modified with nano-TiO₂ and chitosan. *Fibers Polym.* **2007**, *8*, 1–6.
- (46) Song, X.; Liu, A.; Ji, C.; Li, H. The effect of nano-particle concentration and heating time in the anti-crinkle treatment of silk. *Jilin Gongxueyuan Xuebao* **2001**, *22*, 24–27.
- (47) Kumar, S.; Doshi, H.; Srinivasarao, M.; Park, J. O.; Schiraldi, D. A. Fibers from polypropylene/nano carbon fiber composites. *Polymer* **2002**, *43*, 1701–1703.
- (48) Lee, K.; Kim, H.; Khil, M.; Ra, Y.; Lee, D. Characterization of nano-structured poly (ϵ -caprolactone) nonwoven mats via electrospinning. *Polymer* **2003**, *44*, 1287–1294.
- (49) Schaerlaekens, M. Melt extrusion with nano-additives. *Chem. Fib. Int.* **2003**, *53*, 100.
- (50) Jiang, K.; Li, Q.; Fan, S. Nanotechnology: Spinning continuous carbon nanotube yarns. *Nature* **2002**, *419*, 801–801.
- (51) Xin, J.; Daoud, W.; Kong, Y. A new approach to UV-blocking treatment for cotton fabrics. *Text. Res. J.* **2004**, *74*, 97–100.
- (52) Yang, H.; Zhu, S.; Pan, N. Studying the mechanisms of titanium dioxide as ultraviolet-blocking additive for films and fabrics by an improved scheme. *J. Appl. Polym. Sci.* **2004**, *92*, 3201–3210.
- (53) Saito, M. Antibacterial, deodorizing, and UV absorbing materials obtained with zinc oxide (ZnO) coated fabrics. *J. Ind. Text.* **1993**, *23*, 150–164.
- (54) Xiong, M.; Gu, G.; You, B.; Wu, L. Preparation and characterization of poly (styrene butylacrylate) latex/nano-ZnO nanocomposites. *J. Appl. Polym. Sci.* **2003**, *90*, 1923–1931.
- (55) Burniston, N.; Bygott, C.; Stratton, J. Nano technology meets titanium dioxide. *Surf. Coat. Int., Part A* **2004**, *87*, 179–184.
- (56) Daoud, W. A.; Xin, J. H. Low temperature sol-gel processed photocatalytic titania coating. *J. Sol-Gel Sci. Technol.* **2004**, *29*, 25–29.
- (57) Wang, R.; Xin, J. H.; Tao, X. M.; Daoud, W. A. ZnO nanorods grown on cotton fabrics at low temperature. *Chem. Phys. Lett.* **2004**, *398*, 250–255.
- (58) Kathirvelu, S.; D'souza, L.; Dhurai, B. UV protection finishing of textiles using ZnO nanoparticles. *Indian J. Fibre Text Res.* **2009**, *34*, 267–273.
- (59) Moroni, M.; Borrini, D.; Calamai, L.; Dei, L. Ceramic nanomaterials from aqueous and 1, 2-ethanediol supersaturated solutions at high temperature. *J. Colloid Interface Sci.* **2005**, *286*, 543–550.
- (60) Yeo, S. Y.; Lee, H. J.; Jeong, S. H. Preparation of nanocomposite fibers for permanent antibacterial effect. *J. Mater. Sci.* **2003**, *38*, 2143–2147.
- (61) Lee, H.; Yeo, S.; Jeong, S. Antibacterial effect of nanosized silver colloidal solution on textile fabrics. *J. Mater. Sci.* **2003**, *38*, 2199–2204.
- (62) Yeo, S. Y.; Jeong, S. H. Preparation and characterization of polypropylene/silver nanocomposite fibers. *Polym. Int.* **2003**, *52*, 1053–1057.
- (63) Klasen, H. J. Historical review of the use of silver in the treatment of burns. I. *Early uses. Burns* **2000**, *26*, 117–130.
- (64) Feng, Q. L.; Wu, J.; Chen, G. Q.; Cui, F. Z.; Kim, T. N.; Kim, J. O. A mechanistic study of the antibacterial effect of silver ions on *Escherichia coli* and *Staphylococcus aureus*. *J. Biomed. Mater. Res.* **2000**, *52*, 662–668.
- (65) Yamanaka, M.; Hara, K.; Kudo, J. Bactericidal actions of a silver ion solution on *Escherichia coli*, studied by energy-filtering transmission electron microscopy and proteomic analysis. *Appl. Environ. Microbiol.* **2005**, *71*, 7589–7593.
- (66) Nowack, B.; Krug, H. F.; Height, M. 120 years of nanosilver history: implications for policy makers. *Environ. Sci. Technol.* **2011**, *45*, 1177–1183.
- (67) Kumar, R.; Howdle, S.; Münstedt, H. Polyamide/silver antimicrobials: effect of filler types on the silver ion release. *J. Biomed. Mater. Res., Part B* **2005**, *75*, 311–319.
- (68) Pal, S.; Tak, Y. K.; Song, J. M. Does the antibacterial activity of silver nanoparticles depend on the shape of the nanoparticle? A study of the gram-negative bacterium *Escherichia coli*. *Appl. Environ. Microbiol.* **2007**, *73*, 1712–1720.
- (69) Lorenz, C.; Windler, L.; Von Goetz, N.; Lehmann, R.; Schuppler, M.; Hungerbühler, K.; Heuberger, M.; Nowack, B. Characterization of silver release from commercially available functional (nano) textiles. *Chemosphere* **2012**, *89*, 817–824.
- (70) Geranio, L.; Heuberger, M.; Nowack, B. The behavior of silver nanotextiles during washing. *Environ. Sci. Technol.* **2009**, *43*, 8113–8118.
- (71) Benn, T. M.; Westerhoff, P. Nanoparticle silver released into water from commercially available sock fabrics. *Environ. Sci. Technol.* **2008**, *42*, 4133–4139.
- (72) Liu, J.; Hurt, R. H. Ion Release Kinetics and Particle Persistence in Aqueous Nano-Silver Colloids. *Environ. Sci. Technol.* **2010**, *44*, 2169–2175.
- (73) Bozzi, A.; Yuranova, T.; Kiwi, J. Self-cleaning of wool-polyamide and polyester textiles by TiO₂ 2-rutile modification under daylight irradiation at ambient temperature. *J. Photochem. Photobiol., A* **2005**, *172*, 27–34.
- (74) Qi, K.; Chen, X.; Liu, Y.; Xin, J. H.; Mak, C. L.; Daoud, W. A. Facile preparation of anatase/SiO₂ spherical nanocomposites and their application in self-cleaning textiles. *J. Mater. Chem.* **2007**, *17*, 3504–3508.
- (75) Uddin, M. J.; Cesano, F.; Scarano, D.; Bonino, F.; Agostini, G.; Spoto, G.; Bordiga, S.; Zecchina, A. Cotton textile fibres coated by Au/TiO₂ films: Synthesis, characterization and self cleaning properties. *J. Photochem. Photobiol., A* **2008**, *199*, 64–72.
- (76) Wang, R.; Xin, J. H.; Yang, Y.; Liu, H.; Xu, L.; Hu, J. The characteristics and photocatalytic activities of silver doped ZnO nanocrystallites. *Appl. Surf. Sci.* **2004**, *227*, 312–317.
- (77) Çakır, B. A.; Budama, L.; Topel, Ö.; Hoda, N. Synthesis of ZnO nanoparticles using PS-b-PAA reverse micelle cores for UV protective,

self-cleaning and antibacterial textile applications. *Colloids Surf., A* **2012**, *414*, 132–139.

(78) Song, J.; Wang, C.; Hinestroza, J. P. Electrostatic assembly of core-corona silica nanoparticles onto cotton fibers. *Cellulose* **2013**, *20*, 1727–1736.

(79) Song, J.; Birbach, N. L.; Hinestroza, J. P. Deposition of silver nanoparticles on cellulosic fibers via stabilization of carboxymethyl groups. *Cellulose* **2012**, *19*, 411–424.

(80) Simoncic, B.; Tomsic, B. Structures of novel antimicrobial agents for textiles-a review. *Text. Res. J.* **2010**, *80*, 1721.

(81) Tung, W. S.; Daoud, W. A. Self-cleaning fibers via nanotechnology: a virtual reality. *J. Mater. Chem.* **2011**, *21*, 7858–7869.

(82) Halbeisen, M.; Schiff, H. *Chem. Fib. Int.* **2004**, *54*, 378.

(83) Stegmaier, T.; Dauner, M.; Dinkelmann, A.; Scherrieble, A.; von-Armin, V.; Schneider, P.; Planck, H. *Tech. Textiles* **2004**, *47*, 186–191.

(84) Kojima, Y.; Usuki, A.; Kawasumi, M.; Okada, A.; Kurauchi, T.; Kamigaito, O. *J. Polym. Sci., Part A: Polym. Chem.* **1993**, *31*, 1755.

(85) Janowska, G.; Mikołajczyk, T. Thermal properties of fibres from a new polymer of the polyimideamide group. *J. Therm. Anal. Calorim.* **2003**, *71*, 549–558.

(86) Mikołajczyk, T.; Janowska, G.; Urbaniak, W.; Szczapińska, M. *Fib. Text. in East. Eur.* **2004**, *13*, 30.

(87) Malinauskas, A. Chemical deposition of conducting polymers. *Polymer* **2001**, *42*, 3957–3972.

(88) Li, H.; Shi, G.; Ye, W.; Li, C.; Liang, Y. Polypyrrole-carbon fiber composite film prepared by chemical oxidative polymerization of pyrrole. *J. Appl. Polym. Sci.* **1997**, *64*, 2149–2154.

(89) Anbarasan, R.; Vasudevan, T.; Kalaigian, G. P.; Gopalan, A. Chemical grafting of aniline and o-toluidine onto poly (ethylene terephthalate) fiber. *J. Appl. Polym. Sci.* **1999**, *73*, 121–128.

(90) Yin, X.; Kobayashi, K.; Yoshino, K.; Yamamoto, H.; Watanuki, T.; Isa, I. Percolation conduction in polymer composites containing polypyrrole coated insulating polymer fiber and conducting polymer. *Synth. Met.* **1995**, *69*, 367–368.

(91) Bhadani, S. N.; Sen Gupta, S. K.; Sahu, G. C.; Kumari, M. Electrochemical formation of some conducting fibers. *J. Appl. Polym. Sci.* **1996**, *61*, 207–212.

(92) Shim, B. S.; Chen, W.; Doty, C.; Xu, C.; Kotov, N. A. Smart electronic yarns and wearable fabrics for human biomonitoring made by carbon nanotube coating with polyelectrolytes. *Nano Lett.* **2008**, *8*, 4151–4157.

(93) Mattana, G.; Cosseddu, P.; Fraboni, B.; Malliaras, G. G.; Hinestroza, J. P.; Bonfiglio, A. Organic electronics on natural cotton fibres. *Org. Electron.* **2011**, *12*, 2033–2039.

(94) Li, X.; Sun, P.; Fan, L.; Zhu, M.; Wang, K.; Zhong, M.; Wei, J.; Wu, D.; Cheng, Y.; Zhu, H. Multifunctional graphene woven fabrics. *Sci. Rep.* **2012**, *2*, 395.

(95) Shateri-Khalilabad, M.; Yazdanshenas, M. E. Fabricating electroconductive cotton textiles using graphene. *Carbohydr. Polym.* **2013**, *96*, 190–195.

(96) Jost, K.; Perez, C. R.; McDonough, J. K.; Presser, V.; Heon, M.; Dion, G.; Gogotsi, Y. Carbon coated textiles for flexible energy storage. *Energy Environ. Sci.* **2011**, *4*, 5060–5067.

(97) Pan, S.; Lin, H.; Deng, J.; Chen, P.; Chen, X.; Yang, Z.; Peng, H. Novel wearable energy devices based on aligned carbon nanotube fiber textiles. *Adv. Energy Mater.* **2015**, *5*, 401438.

(98) Zhang, D.; Miao, M.; Niu, H.; Wei, Z. Core-spun carbon nanotube yarn supercapacitors for wearable electronic textiles. *ACS Nano* **2014**, *8*, 4571–4579.

(99) Seung, W.; Gupta, M. K.; Lee, K. Y.; Shin, K.-S.; Lee, J.-H.; Kim, T. Y.; Kim, S.; Lin, J.; Kim, J. H.; Kim, S.-W. Nanopatterned Textile-Based Wearable Triboelectric Nanogenerator. *ACS Nano* **2015**, *9*, 3501–3509.

(100) Kim, B. H.; Barnhart, B. S.; Kwon, J. W. Electrostatic power generation using carbon-activated cotton thread on textile. *Micro and Nano Systems Letters* **2015**, *3*, 1–7.

(101) Kim, H.; Kim, S. M.; Son, H.; Kim, H.; Park, B.; Ku, J.; Sohn, J. I.; Im, K.; Jang, J. E.; Park, J.-J. Enhancement of piezoelectricity via

electrostatic effects on a textile platform. *Energy Environ. Sci.* **2012**, *5*, 8932–8936.

(102) Huang, Y.; Hu, H.; Huang, Y.; Zhu, M.; Meng, W.; Liu, C.; Pei, Z.; Hao, C.; Wang, Z.; Zhi, C. From Industrially Weavable and Knittable Highly Conductive Yarns to Large Wearable Energy Storage Textiles. *ACS Nano* **2015**, *9*, 4766.

(103) Huang, Y.; Huang, Y.; Zhu, M.; Meng, W.; Pei, Z.; Liu, C.; Hu, H.; Zhi, C. Magnetic-assisted, self-healable, yarn-based supercapacitor. *ACS Nano* **2015**, *9*, 6242–6251.

(104) Huang, Y.; Tao, J.; Meng, W.; Zhu, M.; Huang, Y.; Fu, Y.; Gao, Y.; Zhi, C. Super-high rate stretchable polypyrrole-based supercapacitors with excellent cycling stability. *Nano Energy* **2015**, *11*, 518–525.

(105) Skorobogatiy, M. Single step fabrication of highly sensitive biosensors. *SPIE Newsroom* **2010**, DOI: 10.1117/2.1201008.002988.

(106) Pone, E.; Dubois, C.; Guo, N.; Gao, Y.; Dupuis, A.; Boismenu, F.; Lacroix, S.; Skorobogatiy, M. Drawing of the hollow all-polymer Bragg fibers. *Opt. Express* **2006**, *14*, 5838–52.

(107) Oh, T. H.; Lee, M. S.; Kim, S. Y.; Shim, H. J. Studies on melt-spinning process of hollow fibers. *J. Appl. Polym. Sci.* **1998**, *68*, 1209–1217.

(108) East, G. C. M. J. E.; Patel, G. C. The dry-jet wet-spinning of an acrylic-fibre yarn. *J. Text. Inst.* **1984**, *75*, 196–200.

(109) Chronakis, I. S. Novel nanocomposites and nanoceramics based on polymer nanofibers using electrospinning process - A review. *J. Mater. Process. Technol.* **2005**, *167*, 283–293.

(110) Teo, W. E.; Ramakrishna, S. A review on electrospinning design and nanofibre assemblies. *Nanotechnology* **2006**, *17*, R89–R106.

(111) Dupuis, A.; Guo, N.; Gao, Y.; Godbout, N.; Lacroix, S.; Dubois, C.; Skorobogatiy, M. Prospective for biodegradable micro-structured optical fibers. *Opt. Lett.* **2007**, *32*, 109–11.

(112) Mazhorova, A.; Markov, A.; Ng, A.; Chinnappan, R.; Skorobogata, O.; Zourob, M.; Skorobogatiy, M. Label-free bacteria detection using evanescent mode of a suspended core terahertz fiber. *Opt. Express* **2012**, *20*, 5344–55.

(113) Dupuis, A.; Guo, N.; Gao, Y.; Skorobogata, O.; Gauvreau, B.; Dubois, C.; Skorobogatiy, M. Fabrication strategies and potential applications of the “green” microstructured optical fibers. *J. Biomed. Opt.* **2008**, *13*, 054003.

(114) Mazhorova, A.; Gu, J. F.; Dupuis, A.; Peccianti, M.; Tsuneyuki, O.; Morandotti, R.; Minamide, H.; Tang, M.; Wang, Y. Y.; Ito, H.; Skorobogatiy, M. Composite THz materials using aligned metallic and semiconductor microwires, experiments and interpretation. *Opt. Express* **2010**, *18*, 24632–24647.

(115) Dupuis, A.; Guo, N.; Gauvreau, B.; Hassani, A.; Pone, E.; Boismenu, F.; Skorobogatiy, M. Guiding in the visible with “colorful” solid-core Bragg fibers. *Opt. Lett.* **2007**, *32*, 2882–4.

(116) Gauvreau, B.; Guo, N.; Schicker, K.; Stoeffler, K.; Boismenu, F.; Ajji, A.; Wingfield, R.; Dubois, C.; Skorobogatiy, M. Color-changing and color-tunable photonic bandgap fiber textiles. *Opt. Express* **2008**, *16*, 15677–93.

(117) Li, J.; Qu, H.; Skorobogatiy, M. Simultaneous monitoring the real and imaginary parts of the analyte refractive index using liquid-core photonic bandgap Bragg fibers. *Opt. Express* **2015**, *23*, 22963–76.

(118) Dupuis, A.; Guo, N.; Gauvreau, B.; Hassani, A.; Pone, E.; Boismenu, F.; Skorobogatiy, M. All-Fiber Spectral Filtering with Solid Core Photonic Band Gap Bragg Fibers. *Conference on Optical Fiber Communication/National Fiber Optic Engineers*, 2008; Vols. 1–8, pp 1954–1956.

(119) Hang, Q.; Ung, B.; Syed, I.; Guo, N.; Skorobogatiy, M. Photonic bandgap fiber bundle spectrometer. *Appl. Opt.* **2010**, *49*, 4791–800.

(120) Qu, H.; Skorobogatiy, M. Liquid-core low-refractive-index-contrast Bragg fiber sensor. *Appl. Phys. Lett.* **2011**, *98*, 201114.

(121) Qu, H.; Ung, B.; Roze, M.; Skorobogatiy, M. All photonic bandgap fiber spectroscopic system for detection of refractive index changes in aqueous analytes. *Sens. Actuators, B* **2012**, *161*, 235–243.

- (122) Gauvreau, B.; Guo, N.; Dubois, C.; Wingfield, R.; Skorobogatiy, M. Color-on-demand photonic textiles. *Textile J.* **2008**, *125*, 70–81.
- (123) Gao, Y.; Guo, N.; Gauvreau, B.; Rajabian, M.; Skorobogata, O.; Pone, E.; Zabeida, O.; Martinu, L.; Dubois, C.; Skorobogatiy, M. Consecutive solvent evaporation and co-rolling techniques for polymer multilayer hollow fiber preform fabrication. *J. Mater. Res.* **2006**, *21*, 2246–2254.
- (124) Gorgutsa, S.; Gu, J. F.; Skorobogatiy, M. A woven 2D touchpad sensor and a 1D slide sensor using soft capacitor fibers. *Smart Mater. Struct.* **2012**, *21*, 015010.
- (125) Gu, J. F.; Gorgutsa, S.; Skorobogatiy, M. Soft capacitor fibers using conductive polymers for electronic textiles. *Smart Mater. Struct.* **2010**, *19*, 115006.
- (126) Gu, J. F.; Gorgutsa, S.; Skorobogatiy, M. Soft capacitor fibers for electronic textiles. *Appl. Phys. Lett.* **2010**, *97*, 133305.
- (127) Qu, H.; Semenikhin, O.; Skorobogatiy, M. Flexible fiber batteries for applications in smart textiles. *Smart Mater. Struct.* **2015**, *24*, 025012.
- (128) Qu, H. B.; Rolland, J.-P.; Vlad, J.; Gohy, A.; Skorobogatiy, J.-F. Flexible fiber batteries for applications in smart textiles. *Smart Mater. Struct.* **2013**, *24*, 1489.
- (129) Liu, Y.; Gorgutsa, S.; Santato, C.; Skorobogatiy, M. Flexible, Solid Electrolyte-Based Lithium Battery Composed of LiFePO₄ Cathode and Li₄Ti₅O₁₂ Anode for Applications in Smart Textiles. *J. Electrochem. Soc.* **2012**, *159*, A349–A356.
- (130) Potschke, P.; Brunig, H.; Janke, A.; Fischer, D.; Jehnichen, D. Orientation of multiwalled carbon nanotubes in composites with polycarbonate by melt spinning. *Polymer* **2005**, *46*, 10355–10363.
- (131) Kim, W.; Kwon, S.; Lee, S.-M.; Kim, J. Y.; Han, Y.; Kim, E.; Choi, K. C.; Park, S.; Park, B.-C. Soft fabric-based flexible organic light-emitting diodes. *Org. Electron.* **2013**, *14*, 3007–3013.
- (132) Khan, A.; Hussain, M.; Abbasi, M. A.; Ibupoto, Z. H.; Nur, O.; Willander, M. Study of transport properties of copper/zinc-oxide-nanorods-based Schottky diode fabricated on textile fabric. *Semicond. Sci. Technol.* **2013**, *28*, 125006.
- (133) Tuniz, A.; Kuhlmeier, B. T.; Lwin, R.; Wang, A.; Anthony, J.; Leonhardt, R.; Fleming, S. C. Drawn metamaterials with plasmonic response at terahertz frequencies. *Appl. Phys. Lett.* **2010**, *96*, 191101.
- (134) Tuniz, A.; Lwin, R.; Argyros, A.; Fleming, S. C.; Pogson, E. M.; Constable, E.; Lewis, R. A.; Kuhlmeier, B. T. Stacked-and-drawn metamaterials with magnetic resonances in the terahertz range. *Opt. Express* **2011**, *19*, 16480–16490.
- (135) Weinberg, B. D.; Milne, G. R.; Andonova, Y. G.; Hajjat, F. M. Internet of Things: Convenience vs. privacy and secrecy. *Business Horizons* **2015**, *58*, 615–624.
- (136) Radic, K. Google Project Glass Debuts at NY Fashion Week, *Branding Magazine*, 2012; <http://www.brandingmagazine.com/2012/09/10/google-project-glass-debuts-at-ny-fashion-week/> (accessed on February 8, 2016).
- (137) Pedersen, I.; Trueman, D. Sergey Brin is Batman: Google's project glass and the instigation of computer adoption in popular culture; *CHI'13 Extended Abstracts on Human Factors in Computing Systems*; ACM, 2013; pp 2089–2098.
- (138) Quinn, B. A note: Hussein Chalayan, fashion and technology. *Fashion Theory* **2002**, *6*, 359–368.
- (139) Sung, J. W.; Heebum, Y.; Gunju, R. Design Transforming Dress based on pneumatic systems. *Journal of Arts and Imaging Science* **2014**, *1*, 5–9.
- (140) Silina, Y.; Haddadi, H. New directions in jewelry: a close look at emerging trends & developments in jewelry-like wearable devices; *Proceedings of the 2015 ACM International Symposium on Wearable Computers*; ACM, 2015; pp 49–56.
- (141) White, J.; Foley, M.; Rowley, A. A Novel Approach to 3D-Printed Fabrics and Garments. *3D Printing and Additive Manufacturing* **2015**, *2*, 145–149.
- (142) Orf, N. D.; Shapira, O.; Sorin, F.; Danto, S.; Baldo, M. A.; Joannopoulos, J. D.; Fink, Y. Fiber draw synthesis. *Proc. Natl. Acad. Sci. U. S. A.* **2011**, *108*, 4743–4747.
- (143) Orf, N. D.; Danto, S.; Shapira, O.; Sorin, F.; Fink, Y.; Joannopoulos, J. D. Fiber Draw Synthesis. Patent Appl. US8663522 B2, 2014.
- (144) O'Mahony, M.; Braddock-Clarke, S. *Techno Textiles 2: Revolutionary Fabrics for Fashion and Design*, 2nd ed.; Thames and Hudson: London, 2005.
- (145) Vasconcellos, F. d. C.; Yetisen, A. K.; Montelongo, Y.; Butt, H.; Grigore, A.; Davidson, C. A. B.; Blyth, J.; Monteiro, M. J.; Wilkinson, T. D.; Lowe, C. R. Printable Surface Holograms via Laser Ablation. *ACS Photonics* **2014**, *1*, 489–495.
- (146) McCann, J.; Bryson, D. *Smart Clothes and Wearable Technology*; Woodhead Publishing Series: Cambridge, UK, 2009.
- (147) Seymour, S. *Fashionable Technology: The Intersection of Design, Fashion, Science, and Technology*; Springer: Vienna, Austria, 2008.
- (148) Hurwitz, M. Safety and Sports Equipment, Apparel and Accessories Using Electroluminescent Fibers for Illumination. Patent Appl. US20010004808 A1, 2000.
- (149) Yei, W. Y. Garment with an Electroluminescent Circuit. Patent Appl. US6116745 A, 2000.
- (150) Mitachi, S.; Shiroishi, D.; Nakagawa, M.; Satoh, K. In Development of a sleep apnea syndrome sensor using optical fibers, Lasers and Electro-Optics Society. *20th Annual Meeting of the IEEE* **2007**, 294–295.
- (151) Huang, C.; Chang, C.; Chen, P. Fabric Material Having Fluorescent Fibers. Patent Appl. US20040157520 A1, 2003.
- (152) Sayed, I. B. J.; Skorobogatiy, M. Jacquard-woven photonic bandgap fiber displays. *Res. J. Textile Apparel* **2010**, *14*.
- (153) Krebber, K.; Liehr, S.; Witt, J. In Smart technical textiles based on fibre optic sensors, 22nd International Conference on Optical Fiber Sensor. *Proc. SPIE* **2012**, 84212A.
- (154) El-Sherif, M. A.; Yuan, J.; Macdiarmid, A. Fiber optic sensors and smart fabrics. *J. Intell. Mater. Syst. Struct.* **2000**, *11*, 407–414.
- (155) Esmailzadeh, H.; Rivard, M.; Arzi, E.; Légaré, F.; Hassani, A. Smart textile plasmonic fiber dew sensors. *Opt. Express* **2015**, *23*, 14981–14992.
- (156) Yang, B.; Tao, X. M.; Yu, J.; Ho, H. Compression force measured by fiber optic smart cellular textile composites. *Text. Res. J.* **2004**, *74*, 305–313.
- (157) Rantala, J.; Hännikäinen, J.; Vanhala, J. Fiber optic sensors for wearable applications. *Personal and Ubiquitous Computing* **2011**, *15*, 85–96.
- (158) Rothmaier, M.; Luong, M. P.; Clemens, F. Textile pressure sensor made of flexible plastic optical fibers. *Sensors* **2008**, *8*, 4318–4329.
- (159) Harlin, A.; Makinen, M.; Vuorivirta, A. Development of polymeric optical fibre fabrics as illumination elements and textile displays. *Autex Res. J.* **2003**, *3*, 1–8.
- (160) Harlin, A.; Myllymaki, H.; Grah, K. Polymeric optical fibres and future prospects in textile integration. *Autex Res. J.* **2002**, *2*, 1.
- (161) Balachandran, R.; Pacheco, D.; Lawandy, N. Photonic textile fibers. *Appl. Opt.* **1996**, *35*, 1991–1994.
- (162) Selm, B.; Gürel, E. A.; Rothmaier, M.; Rossi, R. M.; Scherer, L. J. Polymeric optical fiber fabrics for illumination and sensorial applications in textiles. *J. Intell. Mater. Syst. Struct.* **2010**, *21*, 1061–1071.
- (163) Johnson, S.; Ibanescu, M.; Skorobogatiy, M.; Weisberg, O.; Engeness, T.; Soljacic, M.; Jacobs, S.; Joannopoulos, J.; Fink, Y. Low-loss asymptotically single-mode propagation in large-core OmniGuide fibers. *Opt. Express* **2001**, *9*, 748–79.
- (164) Farandos, N. M.; Yetisen, A. K.; Monteiro, M. J.; Lowe, C. R.; Yun, S. H. Contact lens sensors in ocular diagnostics. *Adv. Healthcare Mater.* **2015**, *4*, 792–810.
- (165) Dong, B. H.; Hinstroza, J. P. Metal nanoparticles on natural cellulose fibers: electrostatic assembly and in situ synthesis. *ACS Appl. Mater. Interfaces* **2009**, *1*, 797–803.
- (166) Hassani, A.; Skorobogatiy, M. Design criteria for micro-structured-optical-fiber-based surface-plasmon-resonance sensors. *J. Opt. Soc. Am. B* **2007**, *24*, 1423–1429.

- (167) Hassani, A.; Skorobogatiy, M. Design of the microstructured optical fiber-based surface plasmon resonance sensors with enhanced microfluidics. *Opt. Express* **2006**, *14*, 11616–11621.
- (168) Gauvreau, B.; Hassani, A.; Fassi Fehri, M.; Kabashin, A.; Skorobogatiy, M. A. Photonic bandgap fiber-based Surface Plasmon Resonance sensors. *Opt. Express* **2007**, *15*, 11413–11426.
- (169) Lin, Y.-C. Characteristics of optical fiber refractive index sensor based on surface plasmon resonance. *Microw. Opt. Technol. Lett.* **2013**, *55*, 574–576.
- (170) Bhatia, P.; Gupta, B. D. Surface-plasmon-resonance-based fiber-optic refractive index sensor: sensitivity enhancement. *Appl. Opt.* **2011**, *50*, 2032–2036.
- (171) Ahmed, R.; Rifat, A. A.; Yetisen, A. K.; Yun, S. H.; Khan, S.; Butt, H. Mode multiplexed waveguide sensor. *J. Electromagnet. Wave* **2015**, *1*.
- (172) Takamatsu, S.; Kobayashi, T.; Shibayama, N.; Miyake, K.; Itoh, T. Fabric pressure sensor array fabricated with die-coating and weaving techniques. *Sens. Actuators, A* **2012**, *184*, 57–63.
- (173) Mattana, G.; Kinkeldei, T.; Leuenberger, D.; Ataman, C.; Ruan, J. J.; Molina-Lopez, F.; Vasquez Quintero, A.; Nisato, G.; Troster, G.; Briand, D. Woven temperature and humidity sensors on flexible plastic substrates for e-textile applications. *IEEE Sens. J.* **2013**, *13*, 3901–3909.
- (174) Cherenack, K.; Zysset, C.; Kinkeldei, T.; Münzenrieder, N.; Tröster, G. Woven electronic fibers with sensing and display functions for smart textiles. *Adv. Mater.* **2010**, *22*, 5178–5182.
- (175) da Silva Pinto, M.; Sierra-Avila, C. A.; Hinestroza, J. P. In situ synthesis of a Cu-BTC metal–organic framework (MOF 199) onto cellulosic fibrous substrates: cotton. *Cellulose* **2012**, *19*, 1771–1779.
- (176) Cherenack, K. H.; Kinkeldei, T.; Zysset, C.; Troster, G. Woven Thin-Film Metal Interconnects. *IEEE Electron Device Lett.* **2010**, *31*, 740–742.
- (177) Ozer, R.; Hinestroza, J. One-step growth of isorecticular luminescent metal–organic frameworks on cotton fibers. *RSC Adv.* **2015**, *5*, 15198–15204.
- (178) Zhukovskiy, M.; Sanchez-Botero, L.; McDonald, M. P.; Hinestroza, J.; Kuno, M. Nanowire-functionalized cotton textiles. *ACS Appl. Mater. Interfaces* **2014**, *6*, 2262–2269.
- (179) Quadros, M. E.; Pierson, R. IV; Tulve, N. S.; Willis, R.; Rogers, K.; Thomas, T. A.; Marr, L. C. Release of silver from nanotechnology-based consumer products for children. *Environ. Sci. Technol.* **2013**, *47*, 8894–8901.
- (180) Kulthong, K.; Srisung, S.; Boonpavanitchakul, K.; Kangwansupamonkon, W.; Maniratanachote, R. Determination of silver nanoparticle release from antibacterial fabrics into artificial sweat. *Part. Fibre Toxicol.* **2010**, *7*, 1–9.
- (181) von Goetz, N.; Lorenz, C.; Windler, L.; Nowack, B.; Heuberger, M.; Hungerbühler, K. Migration of Ag- and TiO₂-(Nano)particles from Textiles into Artificial Sweat under Physical Stress: Experiments and Exposure Modeling. *Environ. Sci. Technol.* **2013**, *47*, 9979–9987.
- (182) Mitrano, D. M.; Rimmle, E.; Wichser, A.; Erni, R.; Height, M.; Nowack, B. Presence of nanoparticles in wash water from conventional silver and nano-silver textiles. *ACS Nano* **2014**, *8*, 7208–7219.
- (183) Davies, P.; Goettl, J.; Sinley, J. Toxicity of silver to rainbow trout (*Salmo gairdneri*). *Water Res.* **1978**, *12*, 113–117.
- (184) Wood, C. M.; Hogstrand, C.; Galvez, F.; Munger, R. The physiology of waterborne silver toxicity in freshwater rainbow trout (*Oncorhynchus mykiss*) 1. The effects of ionic Ag⁺. *Aquat. Toxicol.* **1996**, *35*, 93–109.
- (185) Grosell, M.; Brauner, C. J.; Kelly, S. P.; McGeer, J. C.; Bianchini, A.; Wood, C. M. Physiological responses to acute silver exposure in the freshwater crayfish (*Cambarus diogenes diogenes*)—a model invertebrate? *Environ. Toxicol. Chem.* **2002**, *21*, 369–374.
- (186) Bianchini, A.; Wood, C. M. Physiological effects of chronic silver exposure in *Daphnia magna*. *Comp. Biochem. Physiol., Part C: Toxicol. Pharmacol.* **2002**, *133*, 137–145.
- (187) Choi, O.; Deng, K. K.; Kim, N.-J.; Ross, L.; Surampalli, R. Y.; Hu, Z. The inhibitory effects of silver nanoparticles, silver ions, and silver chloride colloids on microbial growth. *Water Res.* **2008**, *42*, 3066–3074.
- (188) Farkas, J.; Peter, H.; Christian, P.; Urrea, J. A. G.; Hassellöv, M.; Tuoriniemi, J.; Gustafsson, S.; Olsson, E.; Hylland, K.; Thomas, K. V. Characterization of the effluent from a nanosilver producing washing machine. *Environ. Int.* **2011**, *37*, 1057–1062.
- (189) Walser, T.; Demou, E.; Lang, D. J.; Hellweg, S. Prospective Environmental Life Cycle Assessment of Nanosilver T-Shirts. *Environ. Sci. Technol.* **2011**, *45*, 4570–4578.
- (190) Gandhi, N.; Diamond, M. L.; van de Meent, D.; Huijbregts, M. A.; Peijnenburg, W. J.; Guinée, J. New method for calculating comparative toxicity potential of cationic metals in freshwater: application to copper, nickel, and zinc. *Environ. Sci. Technol.* **2010**, *44*, 5195–5201.
- (191) Diamond, M. L.; Gandhi, N.; Adams, W. J.; Atherton, J.; Bhavsar, S. P.; Bulle, C.; Campbell, P. G.; Dubreuil, A.; Fairbrother, A.; Farley, K. The clearwater consensus: the estimation of metal hazard in fresh water. *Int. J. Life Cycle Assess.* **2010**, *15*, 143–147.
- (192) Brouwer, D. Exposure to manufactured nanoparticles in different workplaces. *Toxicology* **2010**, *269*, 120–127.
- (193) Demou, E.; Stark, W. J.; Hellweg, S. Particle emission and exposure during nanoparticle synthesis in research laboratories. *Ann. Occup. Hyg.* **2009**, *53*, 829–838.
- (194) Prweb, LeadFerret Releases a Directory of Contacts in the Fashion and Apparel Industry, 2014; <http://www.prweb.com/releases/leadferret/fashion-apparel-industry/prweb11498609.htm> (accessed on February 8, 2016).
- (195) Remy, N.; Schmidt, J.; Werner, C.; Lu, M. *Unleashing Fashion, Growth City by City*; McKinsey & Company, April 2013.
- (196) Research and Markets, *Smart Textiles Market by Type, Function, Industry, & Geography - Global Forecast to 2020*, July 2015.
- (197) Cientifica. *Business Report: Nanotechnologies for the Textile Market*, April 2012.
- (198) FibeRio Technology Corporation, *Nanofibers*; <http://fiberiotech.com/technology/nanofibers/> (accessed on February 2016).
- (199) PRNewswire. Smart Textiles Market Worth 4,722.81 Million USD by 2020, 2015.
- (200) Cientifica Ltd., *Smart Textiles and Nanotechnologies: Applications Technologies and Markets*, September 2015.
- (201) Yetisen, A. K.; Volpatti, L. R.; Coskun, A. F.; Cho, S.; Kamrani, E.; Butt, H.; Khademhosseini, A.; Yun, S. H. *Entrepreneurship. Lab Chip* **2015**, *15*, 3638–60.
- (202) Gore, R. W. Process for Producing Porous Products. Patent Appl. US 3953566 A, 1976.
- (203) Gore, R. W.; Allen, S. B. Waterproof Laminate. Patent Appl. US419041 A, 1980.
- (204) Nowakowski, N. *Arc'Teryx a perfect fit for Adidas' Salomon business*. Portland Business Journal, November 10, 2002.
- (205) Salomon sold to Amer Sports. Transworld Business August 9, 2005.
- (206) Marmot's Nano AS Jacket: GORE-TEX® Active Products; <http://www.gore-tex.com/product/marmot-nano-as-jacket/1415318110420/> (accessed February 8, 2016).
- (207) Panse, D. Burn Protective Materials. Patent Appl. US 8383528 B2, 2013.
- (208) Xu, P.; Hegenbarth, J. High Purity Perfluoroelastomer Composites and a Process To Produce the Same. Patent Appl. US 20140088235 A1, 2014.
- (209) Gebert, R. Filter Assembly and Mounting Flange Extension for Gas Turbine Filter Assembly. Patent Appl. US 8753414 B2, 2014.
- (210) Cotter, M. A.; Zuckerbrod, D.; Kesler, M. C.; Reynolds, J. S. Insulated Electrical Conductor. Patent Appl. US 5580654 A, 1996.
- (211) Schoeller Textiles AG website; <http://www.schoeller-textiles.com> (accessed on February 8, 2016).
- (212) Greiner, A.; Röcker, T. Polyethylenimine Nanoparticle-Containing Microbicidal Electrospun Polymer Fibers for Textile Applications. Patent Appl. US 20100292623 A1, 2010.
- (213) Tabellion, F.; Steingröver, K.; Waeber, P.; Lottenbach, R. Finishing of Substrates. Patent Appl. US 20110021098 A1, 2011.

- (214) Greiner, A.; Hehl, J. Microbicidal Nano- and Meso-Polymer Fibers Produced from Polymers and Honey, for Textile Applications. Patent Appl. WO2008049251 B1, 2008.
- (215) Performance Textile Leader CRYPTON INC. Purchases NANO-TEX. Reuters, January 6, 2014; <http://www.reuters.com/article/mi-crypton-companies-idUSnBw06S051a+100+BSW20140106> (accessed on February 8, 2016).
- (216) Delattre, J. L.; Hayes, D. J.; Cuiffi, J.; Henry, M.; Kundrat, J.; Carrigan, P. Wash-Durable, Antimicrobial and Antifungal Textile Substrates. Patent Appl. US 8183167 B1, 2012.
- (217) Delattre, J.; Kundrat, J.; Henry, M.; Haupt, R. Wash-Durable Antimicrobial Textiles and Methods of Manufacture. Patent Appl. US 20150233049 A1, 2015.
- (218) AZoNano, *Nanotechnology in Ohio, USA: Market Report*, March 7, 2013; <http://www.azonano.com/article.aspx?ArticleID=3240> (accessed on February 8, 2016).
- (219) Smith, D. J.; Ring, H. Absorbent Non-woven Fibrous Mats and Process for Preparing Same. Patent Appl. US 20090093585 A1, 2009.
- (220) Lademann, J.; Frazier, L. M.; Kataphinan, W. Textile Composite Material Comprising Nanofiber Nonwoven. Patent Appl. US 20110172507 A1, 2011.
- (221) Lademann, J.; Frazier, L. M.; Kataphinan, W. Method for Decontaminating the Skin with Textile Composite Material. Patent Appl. US 20140093548 A1, 2014.
- (222) Chun, I.; Frazier, L. M.; Kataphinan, W. Three-Dimensional Structures for Cell or Tissue Culture. Patent Appl. US 20140363890 A1, 2014.
- (223) Shivers, J. J. C. Segmented Copolyetherester Elastomers. Patent Appl. US 3023192 A, 1962.
- (224) Jayaraman, S.; Park, S.; Rajamanickam, R.; Gopalsamy, C. Fabric or Garment with Integrated Flexible Information Infrastructure. Patent Appl. US 6381482 B1, 2002.
- (225) Jayaraman, S.; Park, S. Fabric-Based Sensor for Monitoring Vital Signs. Patent Appl. US 6970731 B1, 2005.
- (226) Grad View Research. *Smart Textile/Fabric Market Analysis By End-Use (Architecture, Fashion and Entertainment, Medical, Protection & Military, Sports & Fitness, Transportation) and Segment Forecasts to 2020*; January 2014; p 31.
- (227) Alderson, A.; Alderson, K.; Chirima, G. Multi-layer Adhesive Interfaces. Patent Appl. US 20110250445 A1, 2011.
- (228) Alderson, A.; Alderson, K. L.; Davies, P. J.; Smart, G. M. Process for the Preparation of Auxetic Foams. Patent Appl. US 8277719 B2, 2012.
- (229) Alderson, A.; Alderson, K. L.; Hudson, G. D.; Skertchly, D. E. Composite Material. Patent Appl. US 20110281481 A1, 2011.
- (230) Reho, A.; Impiò, J. Wearable Projector and Intelligent Clothing. Patent Appl. US 6830344 B2, 2004.
- (231) Reho, A.; Karinsalo, T. Distance Meter. Patent Appl. US 20060098772 A1, 2006.
- (232) Bianca, D. Bonding with Polyisocyanates. Patent Appl. US3945876 A, 1976.
- (233) Burns, J. T. Delustered Nylon Fiber Containing Segmented Striations of Polypropylene. Patent Appl. US4711812 A, 1987.
- (234) DiCosimo, R.; Gavagan, J. E.; Payne, M. S. Perhydrolase for Enzymatic Peracid Production. Patent Appl. US 8222012 B2, 2012.
- (235) Gale, D. M. Cement Reinforcement. Patent Appl. US4693749 A, 1987.
- (236) Hiramatsu, S.; Moriyama, H.; Asaoka, R.; Morita, K.; Tanaka, T.; Yamada, K.; Obrien, J. P.; Fahnestock, S. R. Silk Thread Containing Spider Thread Protein and Silk Worm Producing the Silk Thread. Patent Appl. US20080287651 A1, 2008.
- (237) Paulson, C. M. Method for Measuring Shape Parameters of Yarn. Patent Appl. US4634280 A, 1987.
- (238) Samuelson, H. V. Hollow Fibers Having Curved Members Projecting Therefore. Patent Appl. US4956237 A, 1990.
- (239) Schubert, K. V.; Liu, A. H.; Scheen, H. Washable Leather with Repellency. Patent Appl. US20080196168 A1, 2008.
- (240) Shah, C. S. Mixed Cross-Section Staple Filament Mixtures and Yarn Therefrom. Patent Appl. US3994122 A, 1976.
- (241) Simmonds, G. E. Staple Yarn Manufacturing Process. Patent Appl. US20090183487 A1, 2009.
- (242) Kay, S.; Ner, Y.; Castellano, L. Devices and Methods for the Production of Microfibers and Nanofibers in a Controlled Environment. Patent Appl. US 20140159262 A1, 2014.
- (243) Peno, E.; Lipton, R.; Kay, S. Method of Making a Device for Use in a Microfiber and/or Nanofiber Producing System. Patent Appl. US 20150013141 A1, 2015.
- (244) Brykalski, M. J.; Terech, J.; Petrovski, D. Environmentally-Conditioned Bed. Patent Appl. US20140310874 A1, 2014.
- (245) Crane, D. T. Crossmember Thermoelectric Generator with Improved Thermal Expansion Protection. Patent Appl. US20130327368 A1, 2013.
- (246) Goenka, L. N. Thermoelectric-Based Air Conditioning System. Patent Appl. US20150176872 A1, 2015.
- (247) Jovic, V.; Poliquin, E. Thermoelectric System with Mechanically Compliant Element. Patent Appl. US20130327369 A1, 2013.
- (248) Lofy, J.; Marquette, D. Devices, Systems and Methods of Cooling the Skin. Patent Appl. US20140260331 A1, 2014.
- (249) Lofy, J.; Marquette, D. Systems and Methods for Cooling Inductive Charging Assemblies. Patent Appl. US20140062392 A1, 2014.
- (250) Lofy, J. D. Condensation and Humidity Sensors for Thermoelectric Devices. Patent Appl. US20150013346 A1, 2015.
- (251) Petrovski, D. Thermal Module. Patent Appl. US20140305625 A1, 2014.
- (252) Ranalli, M. Thermoelectric Assembly Using a Cartridge Support Fixture. Patent Appl. US20140096807 A1, 2014.
- (253) Ranalli, M.; Adldinger, M.; Crane, D. T. High Efficiency Thermoelectric Generation. Patent Appl. US20140034102 A1, 2014.
- (254) Badger, J. P. Recombinant Battery and Plate Separator Therefore. Patent Appl. US 4908282 A, 1990.
- (255) Lawson, G. C.; Wilson, J. C. Filter Paper and Method of Making Same. Patent Appl. US 4161422 A, 1979.
- (256) Lifshutz, N.; Klauber, D.; Gahan, R. High Capacity Filter Medium. Patent Appl. US 20070220852 A1, 2007.
- (257) Lee, J. A. Cotton as a World Crop. In *Cotton*; American Society of Agronomy, Crop Science Society of America, Soil Science Society of America, 1984; pp 1–25.
- (258) Height, M. J. Method for Producing Nanoparticle Loaded Powders Using Flame Spray Pyrolysis and Applications Thereof. Patent Appl. WO2008017176A3, 2008.
- (259) Marte, O.; Meyer, M.; Angehrn, S.; Bienz, A. Water-, Oil-, and Dirt-Repellent Finishes on Fibers and Textile Fabrics. Patent Appl. WO2008124960A1, 2008.
- (260) Marte, O.; Meyer, M.; Height, M. Multifunctional, Responsive Functional Layers on Solid Surfaces and Method for the Production Thereof. Patent Appl. WO2010006457A1, 2010.
- (261) Marte, O.; Meyer, M.; Height, M.; Bienz, A. Carrier System for Subsequent Application onto Substrates and Method Therefore. Patent Appl. WO2010015096A1, 2010.
- (262) Odermatt, E.; Berndt, I.; Centonze, C. R.; Height, M. Textile Implant of Sheath-Core Construction and Method of Forming It. Patent Appl. US20100092531 A1, 2010.
- (263) Centonze, C. R.; Height, M.; Berndt, I.; Odermatt, E. Medical Implant. Patent Appl. WO2009056281A2, 2010.
- (264) Jung, S.; Lauterbach, C. Construction and Electrical Connection Technique in Textile Structures. Patent Appl. US 7022917 B2, 2006.
- (265) Glaser, R. H.; Jung, S.; Lauterbach, C. Modular Micro-electronic-System for Use in Wearable Electronics. Patent Appl. US 20070178716 A1, 2007.
- (266) Orth, M.; Berzowska, J. Electronically Controllable, Visually Dynamic Textile, Fabric, Or Flexible Substrate. Patent Appl. US 20030224155 A1, 2003.
- (267) Orth, M. Electronic Textile Touch Light Controller. Patent Appl. US 7054133 B2, 2006.

- (268) Du Plessis, A. J.; Jessiman, A. W.; Muller, G. J. Position Control Actuator System. Patent Appl. US7246489 B2, 2007.
- (269) Lengyel, A. J.; van Schoor, M. C.; Court, J. R. Aerial Refueling Hose. Patent Appl. US20150096642 A1, 2015.
- (270) Masters, B. P.; Rodgers, J. P.; van Schoor, M. C. Laser Machining of Electroactive Ceramics. Patent Appl. US7205707 B2, 2007.
- (271) Rock, M.; Hunt, V.; Durant, B.; Gilbert, D. Temperature Responsive Smart Textile. Patent Appl. US8389100 B2, 2013.
- (272) Serra, M.; Bromberg, L.; van Reenen Pretorius, J.; Masters, B. Article and Method for Temperature Regulation Using a Thermo-sensitive Reactive Hydrogel Material. Patent Appl. US20040131838 A1, 2004.
- (273) van Schoor, M.; Cutler, A. M.; Muller, G. J.; Lengyel, A.; Radighieri, B. Method and Apparatus for Determining Electrical Properties of Structures. Patent Appl. US7167009 B2, 2007.
- (274) van Schoor, M.; Gilbert, D.; Cutler, A.; Klepper, S. Fluid-Activated Shaft Seal. Patent Appl. US7828299 B2, 2010.
- (275) van Schoor, M.; Klepper, S.; Cutler, A. Bulkhead Seal. Patent Appl. US8608172 B2, 2013.
- (276) van Schoor, M.; Ludlow, C. C.; Klepper, S. A.; Cutler, A. M. Fluid Activated Shaft Seal. Patent Appl. US8419020 B2, 2013.
- (277) van Schoor, M.; Thomas, S. Variable Geometry Heat Sink Assembly. Patent Appl. US20140360699 A1, 2014.
- (278) van Schoor, M. C. Fluid-Activated Shaft Seal. Patent Appl. US7686308 B2, 2010.
- (279) Hu, C.; Offord, D.; Ware, W. Durable Treatment for Fabrics. Patent Appl. US20060021150 A1, 2006.
- (280) Hultin, R. D. L.; Joyce, C.; Brutton, M.; Houchens, K. Educational Tools and Methods for Demonstrating Enhanced Performance Characteristics of a Textile Product to a Person. Patent Appl. US20060110719 A1, 2006.
- (281) Linford, M. L.; Soane, D. S.; Offord, D. A. Water-Repellent and Soil-Resistant Finish for Textiles. Patent Appl. US6855772 B2, 2005.
- (282) Linford, M. R.; Soane, D. S.; Offord, D. A.; Ware, W. Durable Finishes for Textiles. Patent Appl. US6872424 B2, 2005.
- (283) McNamara, J. J.; Ware, W.; Yu, W. Modification of Cellulosic Substrates to Control Body Odor. Patent Appl. US8778321 B2, 2014.
- (284) Offord, D. Odor-Absorbing Cellulosic Fibrous Substrates. Patent Appl. US20060162090 A1, 2006.
- (285) Offord, D.; Ware, W.; Millward, D.; Soane, D.; Young, M. Composite Fibrous Substrates Having Protein Sheaths. Patent Appl. US20040055093 A1, 2004.
- (286) Offord, D.; Ware, W.; Millward, D.; Soane, D.; Young, M. Composite Fibrous Substrates Having Carbohydrate Sheaths. Patent Appl. US20040048541 A1, 2004.
- (287) Offord, D. A. Durable Press Cellulosic Fibrous Substrates with Improved Physical Properties. Patent Appl. US7037441 B2, 2006.
- (288) Offord, D. A.; Ware, W. Methods for Marking Fibrous Substrates. Patent Appl. US7662873 B2, 2010.
- (289) Soane, D.; Houston, M. Microcellular Foam and Foamed Composite Material. Patent Appl. US20020071947 A1, 2002.
- (290) Soane, D.; Linford, M.; Lau, R.; Green, E. Fiber-Reactive Polymeric Dyes. Patent Appl. US20030079302 A1, 2003.
- (291) Soane, D.; Millward, D.; Linford, M.; Lau, R.; Green, E.; Ware, W. Hydrophilic Finish for Fibrous Substrates. Patent Appl. US20060090648 A1, 2006.
- (292) Soane, D.; Offord, D. Oil- and Water-Repellent Finishes for Textiles. Patent Appl. US20030008078 A1, 2003.
- (293) Soane, D.; Ware, W.; Offord, D. Abrasion- and Wrinkle-Resistant Finish for Textiles. Patent Appl. US20020120988 A1, 2002.
- (294) Soane, D. S.; Houston, M. R. Microcellular Foams, Their Method of Production, and Uses and Products Thereof. Patent Appl. US6638984 B2, 2003.
- (295) Soane, D. S.; Linford, M. R.; Offord, D. A.; Millward, D. B.; Ware, W. Hybrid Polymer Materials. Patent Appl. US6517933 B1, 2003.
- (296) Soane, D. S.; Millward, D. B.; Linford, M. R.; Lau, R.; Green, E. G.; Ware, W. Hydrophilic Finish for Fibrous Substrates. Patent Appl. US7427300 B2, 2008.
- (297) Soane, D. S.; Offord, D. A. Modified Textile and Other Materials and Methods for Their Preparation. Patent Appl. US6617267 B2, 2003.
- (298) Soane, D. S.; Offord, D. A.; Linford, M. R.; Millward, D. B.; Ware, W.; Erskine, L.; Green, E.; Lau, R. Nanoparticle-Based Permanent Treatments for Textiles. Patent Appl. US6607994 B2, 2003.
- (299) Stockton, W. B.; Ware, W. Methods for Treating Fabric To Facilitate Moisture Transfer from One Side to the Other. Patent Appl. US7842625 B1, 2010.
- (300) Ware, W.; Soane, D. S.; Millward, D. B.; Linford, M. R. Dye Fixatives. Patent Appl. US6679924 B2, 2004.
- (301) Burkitt, J. Position detection. Patent Appl. US8089336 B2, 2012.
- (302) Crispin, P. G. Sensor Assembly. Patent Appl. US7554051 B2, 2009.
- (303) Graham, M.; Lussey, C. Full-Axis Sensor for Detecting Input Force and Torque. Patent Appl. US7603917 B2, 2009.
- (304) Kilburn, G.; Beagley, T. J. Fabric Bag Including Control Device. Patent Appl. US8300868 B2, 2012.
- (305) Lussey, C. J.; Laughlin, P. J.; Graham, A.; Bloor, D.; Lussey, D. Composite Material. Patent Appl. US20140109698 A1, 2014.
- (306) Lussey, D. Polymer Composition. Patent Appl. US6291568 B1, 2001.
- (307) Lussey, D.; Bloor, D.; Laughlin, P.; Hilsum, C. Polymer Composition. Patent Appl. US8765027 B2, 2014.
- (308) Lussey, D.; Bloor, D.; Laughlin, P. J.; Graham, A.; Hilsum, C. Electrically Responsive Composite Material, A Method of Manufacture and a Transducer Produced Using Said Material. Patent Appl. US8449974 B2, 2013.
- (309) Lussey, D.; Jones, D.; Leftly, S. Flexible Switching Devices. Patent Appl. US7301435 B2, 2007.
- (310) Walkington, S. M. Interfacing Sensors to a Processing Device. Patent Appl. 20100283749 A1, 2010.
- (311) Walkington, S. M. Manually Operable Position Sensor. Patent Appl. US8169295 B2, 2012.
- (312) Walkington, S. M. Woven Manually Operable Input Device. Patent Appl. US8373079 B2, 2013.
- (313) Jayaraman, S.; Park, S.; Rajamanickam, R. Full-Fashioned Weaving Process for Production of a Woven Garment with Intelligence Capability. Patent Appl. US 6145551 A, 2000.
- (314) Jayaraman, S.; Park, S. Method and Apparatus To Create Electrical Junctions for Information Routing in Textile Structures. Patent Appl. US 20080083481 A1, 2008.
- (315) Jayaraman, S.; Park, S. Full-Fashioned Garment in a Fabric and Optionally Having Intelligence Capability. Patent Appl. US 6474367 B1, 2002.
- (316) Jayaraman, S.; Park, S. Full-Fashioned Garment with Sleeves Having Intelligence Capability. Patent Appl. US 6315009 B1, 2001.
- (317) Waeber, P.; Klaus, A.; Marte, W.; Meyer, U. Finishing of Textile Fibers, Tissues and Fabrics. Patent Appl. US 20090137171 A1, 2009.
- (318) Sutter, S.; Lottenbach, R. Method for Producing Temperature-Regulating Surfaces with Phase Change Material. Patent Appl. US 20050227047 A1, 2005.
- (319) Marte, O.; Marte, W.; Angehrn, S.; Meyer, M.; Meyer, U.; Von Arx, U.; Weber, R.; Kunzi, O.; Clivaz, C.; Hochstrasser, M. Finishings For Textile Fibers and Fabrics To Give Hydrophobic Oleophobic and Self-Cleaning Surfaces. Patent Appl. US 20080214075 A1, 2008.
- (320) Marte, O.; Marte, W.; Angehrn, S.; Meyer, M.; Meyer, U.; Von Arx, U.; Weber, R.; Kunzi, O.; Clivaz, C.; Hochstrasser, M. Dressings Which Can Be Applied Several Times to Textile Fibers and Textile Fabrics. Patent Appl. US 20080044580 A1, 2008.
- (321) Hubner, H. J.; Lottenbach, R. Textile Surface. Patent Appl. US 7867571 B2, 2011.

- (322) Holzdörfer, U.; Gaupp, T.; Lottenbach, R.; Hübner, H. J. Reloadable Finishes for Textiles and Formulations for Loading Such Finishes. Patent Appl. US 20130102943 A1, 2013.
- (323) Mestrovic, M. A.; Petersen, P. M.; Cranston, R. W.; Stannard, W. B.; D'Arcy, P. B. System, Garment and Method. Patent Appl. US 20110015498 A1, 2011.
- (324) Esposito, M.; Macagno, M.; Vigano', D. G.; Rizzi, M. M. Methods and Systems for Data Collection, Analysis, Formulation and Reporting of User-Specific Feedback. Patent Appl. US 20150182843 A1, 2015.
- (325) Esposito, M.; Macagno, M.; Vigano', D. G. Sensors, Interfaces and Sensor Systems for Data Collection and Integrated Remote Monitoring of Conditions at or near Body Surfaces. Patent Appl. US 20150177080 A1, 2015.
- (326) Kochman, A.; Gurevich, A. Multi-conductor Soft Heating Element. Patent Appl. US 6452138 B1 2002.
- (327) Kochman, A.; Gurevich, A. Soft Electrical Textile Heater. Patent Appl. US 6369369 B2, 2002.
- (328) Kochman, A.; Kochman, D. Soft Electrical Heater with Continuous Temperature Sensing. Patent Appl. US 6563094 B2, 2003.
- (329) Kochman, A.; Lavit, M.; Kochman, D. Soft Heating Element and Method of Its Electrical Termination. Patent Appl. US 6403935 B2, 2002.
- (330) Kochman, E.; Gerrard, G.; Kochman, D. Heater with Simultaneous Hot Spot and Mechanical Intrusion Protection. Patent Appl. US 6713733 B2, 2005.
- (331) Kochman, E.; Kochman, D. Textile Heater with Continuous Temperature Sensing and Hot Spot Detection. Patent Appl. US 6713733 B2, 2004.
- (332) Burr, S. B. Wearable Article with Band Portion Adapted To Include Textile-Based Electrodes and Method of Making Such Article. Patent Appl. US08082762 B2, 2011.
- (333) Gal, Y. Band-like Garment for Physiological Monitoring. Patent Appl. 20080015454 A1, 2008.
- (334) Hassonjee, Q. N.; Burr, S. B. Functional Textile Structures. Patent Appl. US8709185 B2, 2014.
- (335) Hassonjee, Q. N.; Cera, J.; Bartecki, R. M.; Micka, T. A.; Schultze, C.; Burr, S. B.; Karayianni, E. Textile-Based Electrode. Patent Appl. US8214008 B2, 2012.
- (336) Karayianni, E.; Chaudron, P.; Coulston, G. W. Elastic Composite Yarn, Methods for Making the Same, and Articles Incorporating the Same. Patent Appl. US7765835 B2, 2010.
- (337) Karayianni, E.; Consoli, O.; Coulston, G. W.; Regenstein, K. J. Electrically Conductive Elastic Composite Yarn, Methods for Making the Same, and Articles Incorporating the Same. Patent Appl. US7926254 B2, 2011.
- (338) Karayianni, E.; Coulston, G. W.; Burr, S. B.; Micka, T. A. Functional Elastic Composite Yarn, Methods for Making the Same and Articles Incorporating the Same. Patent Appl. US7946102 B2, 2011.
- (339) Karayianni, E.; Coulston, G. W.; Micka, T. A. Energy Active Composite Yarn, Methods for Making the Same and Articles Incorporating the Same. Patent Appl. US7665288 B2, 2010.
- (340) Karayianni, E.; Munoz, E.; Coulston, G. W.; Burr, S. B.; Micka, T. A. Surface Functional Electro-Textile with Functionality Modulation Capability, Methods for Making the Same, and Applications Incorporating the Same. Patent Appl. US7849888 B2, 2010.
- (341) Kuo, C.; Coulston, G. W. Extended Optical Range System for Monitoring Motion of a Member. Patent Appl. US8428686 B2, 2013.
- (342) Wheeler, B.; Gormley, J.; Micka, T. A. Textile Laminate Structures Including Conductive Elements and Method for Making Such Structures. Patent Appl. US7560671 B2, 2009.
- (343) Wijisiriwardana, R. Physiological Monitoring Wearable Having Three Electrodes. Patent Appl. US20070078324 A1, 2007.
- (344) Sackner, M. A.; Inman, D. M. Systems and Methods for Ambulatory Monitoring of Physiological Signs. Patent Appl. US 7670295 B2, 2010.
- (345) Sackner, M. A.; Inman, D. M. Quantitative Calibration of Breathing Monitors with Transducers Placed on Both Rib Cage and Abdomen. Patent Appl. US 6413225 B1, 2002.
- (346) Sackner, M.; Keenan, D.; Inman, D. M. Method and System for Extracting Cardiac Parameters from Plethysmographic Signals. Patent Appl. US7604603 B2, 2009.
- (347) Keenan, D.; Coyle, M. Method and System for Processing Data from Ambulatory Physiological Monitoring. Patent Appl. US 20050240087 A1, 2005.
- (348) Istook, C. L. Composite Elastic and Wire Fabric for Physiological Monitoring Apparel. Patent Appl. US 6341504 B1, 2002.
- (349) Gal, Y. Physiological Signal Processing Devices and Associated Processing Methods. Patent Appl. US 20070270671 A1, 2007.
- (350) Coyle, M.; Keenan, D. B.; Derchak, P. A.; Sackner, M.; Wilhelm, F.; Gilroy, K.; Gummels, E. M.; Inman, D. M.; Kennedy, P.; Mitchnick, M. Systems and Methods for Respiratory Event Detection. Patent Appl. US 7267652 B2, 2007.
- (351) Coyle, M.; Derchak, P. A.; Myers, L. J. Systems and Methods for Monitoring Cough. Patent Appl. US 7727161 B2, 2010.
- (352) Arredondo, J. G.; Barrionuevo, S. G. Sensor Apparatus Adapted To Be Incorporated in a Garment. Patent Appl. US 20130041272 A1, 2013.
- (353) Bacino, J. Porous PTFE Film and a Manufacturing Method Therefore. Patent Appl. US5476589 A, 1995.
- (354) Berman, A. B. Resorbable Interposition Arthroplasty Implant. Patent Appl. US6017366 A, 2000.
- (355) Branca, P. A.; Hubis, D. E.; Buerger, W.; Rudolf, C.; Tillmanns, R. Strong, Air Permeable Membranes of Polytetrafluoroethylene. Patent Appl. US5814405 A, 1998.
- (356) Campbell, C. V.; Chastain, J. H.; Kovach, L. J.; Laguna, A. J.; Pond, D. B. Method of Insitu Bypass To Hold Open Venous Valves. Patent Appl. US5843171 A, 1998.
- (357) Culler, G. D.; Pheris, J. G.; Regester, J. M. Invertible Camouflage Construction. Patent Appl. US20130040114 A1, 2013.
- (358) Dolan, J.; Murphy, M.; Minor, R.; Shahkarami, S.; Krummel, J. Protective Undergarment. Patent Appl. US20130273343 A1, 2013.
- (359) Gifford, R. B.; Keough, M. Vent Installation Method. Patent Appl. US8968063 B2, 2015.
- (360) Gore, R. W. Porous Products and Process Therefore. Patent Appl. US4187390 A, 1980.
- (361) Gore, S. A.; Zador, D. T. Waterproof Shoe and Insole Strip. Patent Appl. US5426869 A, 1995.
- (362) Hanrahan, J. R. Electrically Conductive Composite Article. Patent Appl. US6210789 B1, 2001.
- (363) Hendershot, W. J.; McDonald, M. L.; Timian, V. J. Method of Ultrasonically Welding Articles of Porous Polytetrafluoroethylene. Patent Appl. US5746856 A, 1998.
- (364) Holliday, A. J. Venting Array and Manufacturing Method. Patent Appl. US20150114555 A1, 2015.
- (365) Hubner, T.; Bleimhofer, W. Wearing Apparel with Ventilation Material. Patent Appl. US5014363 A, 1991.
- (366) Pacanowsky, D. J.; Williams, R. S. Waterproof Breathable Sock. Patent Appl. US4809447 A, 1989.
- (367) Scanlon, J. J.; Wnenschak, R. M.; Giannetta, R. W. Filter for a Wet/Dry Vacuum Cleaner for Wet Material Collection. Patent Appl. US5783086 A, 1998.
- (368) Sharber, N. J.; Moll, K. W.; Schwarz, K. E.; Sparling, C. M. Carvable PTFE Implant Material. Patent Appl. US6075180 A, 2000.
- (369) Thompson, R. M. Method To Reduce the Damage Caused by Ionizing Radiation to Polyurethane/Porous Expanded Polytetrafluoroethylene Composites by Use of Hindered Phenols. Patent Appl. US4963416 A, 1990.
- (370) Wiener, R. J. Strobel Footwear Construction. Patent Appl. US20130232818 A1, 2013.
- (371) Yamazaki, E. Production of Porous Sintered PTFE Products. Patent Appl. US4110392 A, 1978.
- (372) Innovation in Wearable Tech, Cambridge Consultants; <http://www.cambridgeconsultants.com/media/press-releases/innovation-wearable-tech> (accessed on February 8, 2016).
- (373) Koyama, Y.; Nishiyama, M.; Watanabe, K. In Multi-channel measurement for hetero-core optical fiber sensor by using CMOS

camera, Fifth Asia Pacific Optical Sensors Conference. *Proc. SPIE* **2015**, 965525.

(374) Shah, R.; Agrawal, Y. Introduction to fiber optics: Sensors for biomedical applications. *Indian J. Pharm. Sci.* **2011**, 73, 17.

(375) Cochrane, C.; Meunier, L.; Kelly, F. M.; Koncar, V. Flexible displays for smart clothing: Part I-Overview. *Indian J. Fibre Textile Res.* **2011**, 36, 422.

(376) Lee, J.-H.; Liu, D. N.; Wu, S.-T. *Introduction to Flat Panel Displays*; John Wiley & Sons: Chichester, UK, 2008; Vol. 20.

(377) Geffroy, B.; Le Roy, P.; Prat, C. Organic light-emitting diode (OLED) technology: materials, devices and display technologies. *Polym. Int.* **2006**, 55, 572–582.

(378) Kim, T.-H.; Cho, K.-S.; Lee, E. K.; Lee, S. J.; Chae, J.; Kim, J. W.; Kim, D. H.; Kwon, J.-Y.; Amarutunga, G.; Lee, S. Y. Full-colour quantum dot displays fabricated by transfer printing. *Nat. Photonics* **2011**, 5, 176–182.

(379) Kim, L.; Anikeeva, P. O.; Coe-Sullivan, S. A.; Steckel, J. S.; Bawendi, M. G.; Bulovic, V. Contact printing of quantum dot light-emitting devices. *Nano Lett.* **2008**, 8, 4513–4517.

(380) Butt, H.; Yetisen, A. K.; Ahmed, R.; Yun, S. H.; Dai, Q. Carbon nanotube biconvex microcavities. *Appl. Phys. Lett.* **2015**, 106, 121108.

(381) Kong, X.-T.; Khan, A. A.; Kidambi, P. R.; Deng, S.; Yetisen, A. K.; Dlubak, B.; Hiralal, P.; Montelongo, Y.; Bowen, J.; Xavier, S.; Jiang, K.; Amarutunga, G. A. J.; Hofmann, S.; Wilkinson, T. D.; Dai, Q.; Butt, H. Graphene-Based Ultrathin Flat Lenses. *ACS Photonics* **2015**, 2, 200–207.

(382) Deng, S.; Yetisen, A. K.; Jiang, K.; Butt, H. Computational modelling of a graphene Fresnel lens on different substrates. *RSC Adv.* **2014**, 4, 30050–30058.

(383) Kong, X.-T.; Butt, H.; Yetisen, A. K.; Kangwanwatana, C.; Montelongo, Y.; Deng, S.; Cruz Vasconcellos, F. d.; Qasim, M. M.; Wilkinson, T. D.; Dai, Q. Enhanced reflection from inverse tapered nanocone arrays. *Appl. Phys. Lett.* **2014**, 105, 053108.

(384) Joannopoulos, J. D.; Johnson, S. G.; Winn, J. N.; Meade, R. D. *Photonic Crystals: Molding the Flow of Light*, 2nd ed., Princeton University Press: Princeton, NJ, 2008.

(385) Yetisen, A. K.; Butt, H.; Volpatti, L. R.; Pavlichenko, I.; Humar, M.; Kwok, S. J. J.; Koo, H.; Kim, K. S.; Naydenova, I.; Khademhosseini, A.; Hahn, S. K.; Yun, S. H. Photonic hydrogel sensors. *Biotechnol. Adv.* **2015**, DOI: 10.1016/j.biotechadv.2015.10.005.

(386) Butt, H.; Yetisen, A. K.; Mistry, D.; Khan, S.; Hassan, M. U.; Yun, S. H. Morpho Butterfly Inspired Nanostructures. *Adv. Opt. Mater.* **2016**, DOI: 10.1002/adom.201500658.

(387) You, A.; Cao, Y.; Cao, G. Facile fabrication of a magnetically assembled colloidal photonic crystal film via radical polymerization. *RSC Adv.* **2015**, 5, 93945–93950.

(388) Iliw, R.; Etrich, C.; Peschel, U.; Lederer, F.; Augustin, M.; Fuchs, H.-J.; Schelle, D.; Kley, E.-B.; Nolte, S.; Tünnermann, A. Diffractionless propagation of light in a low-index photonic-crystal film. *Appl. Phys. Lett.* **2004**, 85, 5854.

(389) Xuan, R.; Wu, Q.; Yin, Y.; Ge, J. Magnetically assembled photonic crystal film for humidity sensing. *J. Mater. Chem.* **2011**, 21, 3672–3676.

(390) Arsenaault, A.; Ozin, G. A.; Von Freymann, G. Compressible Photonic Crystal. Patent Appl. US8676016 B2, 2014.

(391) Tsangarides, C. P.; Yetisen, A. K.; da Cruz Vasconcellos, F.; Montelongo, Y.; Qasim, M. M.; Wilkinson, T. D.; Lowe, C. R.; Butt, H. Computational modelling and characterisation of nanoparticle-based tuneable photonic crystal sensors. *RSC Adv.* **2014**, 4, 10454–10461.

(392) Zhao, Q.; Yetisen, A. K.; Sabouri, A.; Yun, S. H.; Butt, H. Printable Nanophotonic Devices via Holographic Laser Ablation. *ACS Nano* **2015**, 9, 9062–9069.

(393) Zhao, Q.; Yetisen, A. K.; Anthony, C. J.; Fowler, W. R.; Yun, S. H.; Butt, H. Printable ink holograms. *Appl. Phys. Lett.* **2015**, 107, 041115.

(394) Toal, V. *Introduction to Holography*; CRC Press: Boca Raton, FL, 2011.

(395) Butt, H.; Montelongo, Y.; Butler, T.; Rajesekharan, R.; Dai, Q.; Shiva-Reddy, S. G.; Wilkinson, T. D.; Amarutunga, G. A. Carbon nanotube based high resolution holograms. *Adv. Mater.* **2012**, 24, OP331–OP336.

(396) Microsoft HoloLens; <http://www.microsoft.com/microsoft-hololens/en-us> (accessed February 8, 2016).

(397) Yetisen, A. K.; Naydenova, I.; da Cruz Vasconcellos, F.; Blyth, J.; Lowe, C. R. Holographic Sensors: Three-Dimensional Analyte-Sensitive Nanostructures and Their Applications. *Chem. Rev.* **2014**, 114, 10654–10696.

(398) Yetisen, A. K.; Montelongo, Y.; Qasim, M. M.; Butt, H.; Wilkinson, T. D.; Monteiro, M. J.; Yun, S. H. Photonic Nanosensor for Colorimetric Detection of Metal Ions. *Anal. Chem.* **2015**, 87, 5101–5108.

(399) Yetisen, A. K.; Montelongo, Y.; da Cruz Vasconcellos, F.; Martinez-Hurtado, J. L.; Neupane, S.; Butt, H.; Qasim, M. M.; Blyth, J.; Burling, K.; Carmody, J. B.; Evans, M.; Wilkinson, T. D.; Kubota, L. T.; Monteiro, M. J.; Lowe, C. R. Reusable, robust, and accurate laser-generated photonic nanosensor. *Nano Lett.* **2014**, 14, 3587–93.

(400) Yetisen, A. K.; Butt, H.; da Cruz Vasconcellos, F.; Montelongo, Y.; Davidson, C. A.; Blyth, J.; Chan, L.; Carmody, J. B.; Vignolini, S.; Steiner, U. Light-Directed Writing of Chemically Tunable Narrow-Band Holographic Sensors. *Adv. Opt. Mater.* **2014**, 2, 250–254.

(401) Yetisen, A. K.; Montelongo, Y.; Farandos, N. M.; Naydenova, I.; Lowe, C. R.; Yun, S. H. Mechanism of multiple grating formation in high-energy recording of holographic sensors. *Appl. Phys. Lett.* **2014**, 105, 261106.

(402) Yetisen, A. K.; Qasim, M. M.; Nosheen, S.; Wilkinson, T. D.; Lowe, C. R. Pulsed laser writing of holographic nanosensors. *J. Mater. Chem. C* **2014**, 2, 3569–3576.

(403) Smith, D. R.; Pendry, J. B.; Wiltshire, M. C. Metamaterials and negative refractive index. *Science* **2004**, 305, 788–792.

(404) Schurig, D.; Mock, J.; Justice, B.; Cummer, S. A.; Pendry, J. B.; Starr, A.; Smith, D. Metamaterial electromagnetic cloak at microwave frequencies. *Science* **2006**, 314, 977–980.

(405) Liang, D.; Gu, J.; Han, J.; Yang, Y.; Zhang, S.; Zhang, W. Robust large dimension terahertz cloaking. *Adv. Mater.* **2012**, 24, 916–921.

(406) Zhou, F.; Bao, Y.; Cao, W.; Stuart, C. T.; Gu, J.; Zhang, W.; Sun, C. Hiding a realistic object using a broadband terahertz invisibility cloak. *Sci. Rep.* **2011**, 1, 00078.

(407) Upadhyay, A.; Prajapati, Y.; Singh, V.; Saini, J. Comprehensive study of reverse index waveguide based sensor with metamaterial as a guiding layer. *Opt. Commun.* **2015**, 348, 71–76.

(408) Li, X.; Tian, J.; Shen, W. Thread as a versatile material for low-cost microfluidic diagnostics. *ACS Appl. Mater. Interfaces* **2010**, 2, 1–6.

(409) Safavieh, R.; Zhou, G. Z.; Juncker, D. Microfluidics made of yarns and knots: from fundamental properties to simple networks and operations. *Lab Chip* **2011**, 11, 2618–2624.

(410) Nilghaz, A.; Ballerini, D.; Shen, W. Exploration of microfluidic devices based on multi-filament threads and textiles: A review. *Biomechanics* **2013**, 7, 051501.

(411) Yetisen, A. K.; Akram, M. S.; Lowe, C. R. Paper-based microfluidic point-of-care diagnostic devices. *Lab Chip* **2013**, 13, 2210–51.

(412) Yetisen, A. K.; Volpatti, L. R. Patent protection and licensing in microfluidics. *Lab Chip* **2014**, 14, 2217–2225.

(413) Volpatti, L. R.; Yetisen, A. K. Commercialization of microfluidic devices. *Trends Biotechnol.* **2014**, 32, 347–50.

(414) Zhou, G.; Mao, X.; Juncker, D. Immunochromatographic assay on thread. *Anal. Chem.* **2012**, 84, 7736–7743.

(415) Akram, M. S.; Daly, R.; da Cruz Vasconcellos, F.; Yetisen, A.; Hutchings, I.; Hall, E. A. H. Applications of Paper-Based Diagnostics. In *Lab-on-a-Chip Devices and Micro-Total Analysis Systems*; Castillo-León, J., Svendsen, W. E., Eds.; Springer International Publishing: Cham, Switzerland, 2015; pp 161–195.

(416) Yetisen, A. K. Point-of-Care Diagnostics. In *Holographic Sensors*; Springer International Publishing: Cham, Switzerland, 2015; pp 1–25.

- (417) Yetisen, A. K.; Davis, J.; Coskun, A. F.; Church, G. M.; Yun, S. H. *Trends Biotechnol.* **2015**, *33*, 724–734.
- (418) Yetisen, A. K.; Coskun, A. F.; England, G.; Cho, S.; Butt, H.; Hurwitz, J.; Kolle, M.; Khademhosseini, A.; Hart, A. J.; Folch, A.; Yun, S. H. Art on the Nanoscale and Beyond. *Adv. Mater.* **2015**, DOI: 10.1002/adma.201502382.
- (419) Yetisen, A. K.; Martinez-Hurtado, J. L.; Garcia-Melendrez, A.; da Cruz Vasconcellos, F.; Lowe, C. R. A smartphone algorithm with inter-phone repeatability for the analysis of colorimetric tests. *Sens. Actuators, B* **2014**, *196*, 156–160.
- (420) Yetisen, A. K.; Martinez-Hurtado, J. L.; da Cruz Vasconcellos, F.; Simsekler, M. C.; Akram, M. S.; Lowe, C. R. The regulation of mobile medical applications. *Lab Chip* **2014**, *14*, 833–40.
- (421) Yetisen, A. K. Mobile Medical Applications. In *Holographic Sensors*; Springer International Publishing: Cham, Switzerland, 2015; pp 135–148.
- (422) ISO Standards Catalogue: ISO/TC38 Textile; International Organization for Standardization, 2015.
- (423) Lin, B.; Moubarak, M. Decomposition analysis: Change of carbon dioxide emissions in the Chinese textile industry. *Renewable Sustainable Energy Rev.* **2013**, *26*, 389–396.
- (424) Roy, S.; Dhar, M.; Krishna, P. V.; May, R. *Report, Cutting Cotton Carbon Emissions: Findings from Warangal, India*; Agarwal, B., Jeffries, B., Eds.; World Wide Fund for Nature, 2013.
- (425) Kant, R. Textile dyeing industry an environmental hazard. *Nat. Sci.* **2012**, *4*, 22–26.
- (426) Kanagaraj, J.; Chandra Babu, N. K.; Mandal, A. B. Recovery and reuse of chromium from chrome tanning waste water aiming towards zero discharge of pollution. *J. Cleaner Prod.* **2008**, *16*, 1807–1813.
- (427) Leire, C.; Thidell, Å. Product-related environmental information to guide consumer purchases – a review and analysis of research on perceptions, understanding and use among Nordic consumers. *J. Cleaner Prod.* **2005**, *13*, 1061–1070.
- (428) Pickett-Baker, J.; Ozaki, R. Pro-environmental products: marketing influence on consumer purchase decision. *J. Consum. Mark.* **2008**, *25*, 281–293.
- (429) Young, W.; Hwang, K.; McDonald, S.; Oates, C. J. Sustainable consumption: green consumer behaviour when purchasing products. *Sustainable Development* **2010**, *18*, 20–31.
- (430) Becker-Olsen, K. L.; Cudmore, B. A.; Hill, R. P. The impact of perceived corporate social responsibility on consumer behavior. *J. Bus. Res.* **2006**, *59*, 46–53.
- (431) Mainieri, T.; Barnett, E. G.; Valdero, T. R.; Unipan, J. B.; Oskamp, S. Green Buying: The Influence of Environmental Concern on Consumer Behavior. *J. Soc. Psychol.* **1997**, *137*, 189–204.